



**University of
Zurich**^{UZH}

**Zurich Open Repository and
Archive**

University of Zurich
University Library
Strickhofstrasse 39
CH-8057 Zurich
www.zora.uzh.ch

Year: 2021

**The influence of zirconia veneer thickness on the degree of conversion of
resin-matrix cements: an integrative review**

Tafur-Zelada, Christie M ; Carvalho, Oscar ; Silva, Filipe S ; Henriques, Bruno ; Özcan, Mutlu ; Souza, Júlio C M

DOI: <https://doi.org/10.1007/s00784-021-03904-w>

Posted at the Zurich Open Repository and Archive, University of Zurich

ZORA URL: <https://doi.org/10.5167/uzh-216358>

Journal Article

Accepted Version

Originally published at:

Tafur-Zelada, Christie M; Carvalho, Oscar; Silva, Filipe S; Henriques, Bruno; Özcan, Mutlu; Souza, Júlio C M (2021). The influence of zirconia veneer thickness on the degree of conversion of resin-matrix cements: an integrative review. *Clinical Oral Investigations*, 25(6):3395-3408.

DOI: <https://doi.org/10.1007/s00784-021-03904-w>

The influence of zirconia veneer thickness on the degree of conversion of resin-matrix cements: an integrative review

Christie M. Tafur-Zelada^a, Oscar Carvalho^b, Filipe Silva^b, Bruno Henriques^{b,c}, Mutlu Özcan^d, Júlio C. M. Souza^{a,b}

^aDepartment of Dental Sciences, University Institute of Health Sciences (IUCS), CESPU, 4585-116 Gandra PRD, Portugal

^bCenter for MicroElectromechanical Systems (CMEMS-UMINHO), University of Minho, 4800-058 Guimarães, Portugal

^cPost-graduate programa in Mechanical Engineering, Departament of Mechanical Engineering (EMC), Universidade Federal de Santa Catarina (UFSC), 88040-900, Florianopolis, SC, Brazil

^dDepartment of Biomaterials, Center of Dental Medicine, University of Zurich, Switzerland

Corresponding author:

Julio C. M. Souza, PhD, MSc, DDS

Rua Central de Gandra, Gandra PRD, 4585-116, Portugal

Department of Dental Sciences, University Institute of Health Sciences (IUCS), CESPU

Email: jsouza@dem.uminho.pt

ORCID ID: 0001-7999-4009

Phone: +351 224157100

Abstract

Objective: The aim of this study was to conduct an integrative review on the influence of the zirconia veneer thickness on the degree of conversion of resin-matrix cements.

Materials and method: An electronic search was performed on PUBMED using a combination of the following search items: zirconia, thickness, veneer, degree of conversion, resin cement, light curing, and polymerization. Articles published in the English language, up to July 2020 were included regarding the influence of ceramic veneer thickness on the degree of conversion of resin cements. Randomized controlled trials and prospective cohort studies were also evaluated.

Results: Of the 21 studies selected, 9 investigated the light-curing effect while five other articles evaluated the ceramic translucency. Three studies evaluated the degree of conversion of the resin-matrix cement and then four articles assessed the veneer thickness.

Results revealed a significant decrease of light transmission through the zirconia with a thickness ranging from 0.1 to 1.5 mm results. However, the ultra-thin thickness around 0.1 and 0.3 mm allowed a full polymerization of the dual-curing resin-matrix cement resulting in the maintenance of the interface properties. The light-curing process of resin cement is also affected by the shade, chemical composition, and microstructure of zirconia and resin cement. Optimum conditions of light-curing are required to reach the threshold intensity of light and energy for polymerization of resin-matrix cements.

Conclusions: The increase in zirconia veneer thickness negatively affect the degree of conversion of resin-matrix cements. Also, shade and microstructure are key factor to improve the light curing of resin cements.

Clinical relevance: Clinicians should consider the zirconia thickness on resin-based cementation since a higher veneer thickness can negatively affect the light irradiation intensity to the dual-curing resin-matrix cement. Thus, the degree of conversion of the resin-matrix cement decreases leading to a low chemical stability (e.g. color instability) and poor mechanical properties.

Keywords: degree of conversion, polymerization, resin cement, thickness, translucency, zirconia veneer

1. Introduction

Recently, the demand for esthetics has led to the development of high strength materials such as zirconia-based structures for oral rehabilitation [1–3]. Clinical cases with zirconia-based veneers have been reported in literature although failures can occur by veneer chipping or low adhesion to the teeth structures [4–7]. The ceramic thickness, microstructure, and the resin-matrix cement have an important role on the light curing, translucency, and color of the restoration [8–12]. A low degree of conversion of the resin-matrix cement is dependent on the cement properties itself, ceramic veneer thickness, and polymerization procedure [10, 13–15].

Yttria-stabilized tetragonal zirconia polycrystalline (Y-TZP) is a high-strength polycrystalline zirconia developed for different industrial applications including biomedical materials such as prosthetics and implants [1, 16]. In dentistry, zirconia-based materials often contain zirconium dioxide named zirconia and 3-7mol% yttria in the chemical composition to maintain the tetragonal phase (around 50vol%) that determine the mechanical properties of the prosthetic structures [1, 2]. The first generation of yttria-stabilized tetragonal zirconia polycrystal (3YTZP) with 3-5% yttria

has a three-point bending strength of around 1200 ± 130 MPa, fracture toughness at 9 ± 0.34 MPa.m^{1/2}, and elastic modulus of around 240 ± 9.5 GPa [1, 3, 17]. Due to its higher opacity, 3Y-TZP has been used as a prosthetic framework material in which a veneer glass-ceramics can be applied for aesthetic improvements [8, 9, 18–20]. Thus, 3Y-TZP frameworks have the convenient opacity to mask all shades of discolored background which involve also metallic abutments. Nevertheless, light transmission is reduced because the opaque tetragonal phase [8, 9, 18–20]. Current changes in the formulation of zirconia resulted in a recent class of monolithic highly translucent zirconia with a different molecular structure and physical properties and a more attractive aesthetic appearance [1]. Monolithic translucent zirconia ceramics contain approximately 5-8mol% yttria and above 50% of cubic crystals, which increase translucency. However, such changes in the chemical composition and microstructure are detrimental to the mechanical properties of the material [1, 2, 16].

Thus, polycrystalline microstructure of the 3YTZP veneer and the increase in thickness negatively affect the light-curing of the resin-matrix cement [10, 18, 21, 22]. Indeed, low transmittance is expected through thick layers of YTZP, which explains the relatively light irradiation procedures used when cementing light-activated resin-matrix compounds [12, 14]. Over the years, several types of resin-matrix cement materials have been developed for the adhesion of ceramics and therefore methacrylate-based cements are the first choice material for joining dental structures and ceramic restorations. The chemical composition of resin-matrix cements involves the presence of Bis-GMA, TEGDMA, UDMA embedding inorganic fillers such as colloidal silica, ytterbium, or barium glass [6, 10, 22]. The resin-matrix composites possess the following properties which are important for cementing ceramic veneers: low solubility, translucency,

flowability, easy handling, and elasticity [4, 6, 10, 23, 24]. Also, the solubility of the resin-matrix cement is lower than those recorded for conventional cements that promote a long-term sealing at the marginal region of the restoration [4, 6, 10, 23, 24]. Regarding the polymerization, there are three types of resin-matrix cements: light-curing, self-curing, and dual-curing [6, 10, 22]. Light-curing and dual-curing methods are used for veneer adhesion with resin-matrix cements and therefore the light-curing method has the main advantage on the working time for cementation and removal of remnant cement at the veneer margins [10, 22, 25]. Nevertheless, light-curing procedure cannot guarantee a high degree of conversion of the resin-matrix cement considering other factors such as veneer type and thickness, type of resin-matrix cement, and polymerization procedure [15, 24, 26]. On the other hand, the dual-cure resin-matrix cements combine the desirable properties of chemical and light-curing materials to guarantee the degree of conversion of monomers in the case of insufficient light transmission [15, 24, 26]. The major problem of having an inadequate polymerization is the low degree of conversion leading to a decrease in physical properties and color stability [10, 24, 27, 28]. The degree of conversion of the organic matrix of resin cements must be enhanced that corresponds to an efficient polymerization of resin-matrix materials. As a result, the strength of the adhesive interface is increased leading to a long term performance of the zirconia-based prosthetics [10, 24, 27, 28].

The aim of the present study was to conduct an integrative review of the literature on the influence of the zirconia veneer on the degree of conversion of the resin-matrix cements. It was hypothesized that thick zirconia-based restorations attenuate the light irradiation towards to the resin-matrix cements during the light-curing procedure. Also,

the microstructure of zirconia can affect the light irradiation and therefore the light-curing procedure could be adjusted for different zirconia restorations.

2. Method

2.1. Information sources and search strategy

A literature search was performed on PubMed (via National Library of Medicine) considering such database includes the major articles in the field of dentistry and biomaterials. The present method was performed in accordance with the search strategy applied in previous studies on integrative or systematic reviews [7, 29–31]. The following combination of search terms was applied in this study: “Zirconia” OR “YTZP” AND “Translucency” OR “thickness” AND “resin cement” OR “Adhesive” AND “degree of conversion” OR “polymerization” OR “light curing”. The inclusion criteria involved articles published in the English language, up to July 2020, reporting the influence of ceramic veneer thickness on the degree of conversion of resin cements. The eligibility inclusion criteria used for article searches also involved: *in vitro* studies; meta-analyses; randomized controlled trials; and prospective cohort studies. Ongoing studies were searched in the following clinical trial registries: Current Controlled Trials, International Clinical trials registry platform, ClinicalTrials.gov, ReBEC, and EU Clinical Trials Register. Also, a hand-search was performed on the reference lists of all primary sources and eligible studies of this systematic review for additional relevant publications. The exclusion criteria were the following: papers without abstract; case report with short follow-up period; articles assessing only the light transmission through other glass ceramic materials. Studies based on publication date were not restricted during the search process.

2.2. Study selection and data collection process

The articles retrieved by the search process were evaluated in three steps. Studies were primarily scanned for relevance by title, and the abstracts of those that were not excluded at this stage were assessed. Two of the authors (JCMS, CMTZ) independently analyzed the titles and abstracts of potentially relevant articles although a third author (BH) performed a final evaluation in case of disagreement. The total of articles was compiled for each combination of key terms and therefore the duplicates were removed using Mendeley citation manager. The second step comprised the evaluation of the abstracts and non-excluded articles, according to the eligibility criteria in the abstract review. A preliminary evaluation of the abstracts was carried out to establish whether the articles met the purpose of the study. Selected articles were individually read and evaluated concerning the purpose of this study. At last, the eligible articles received a study identification label, combining first author and year of publication. The following factors were retrieved for this review: author names, journal, publication year, purpose, type of resin cement, thickness of zirconia veneer, light curing procedures, degree of conversion of the resin cement, physical properties. PICO question was adjusted to the issue where “P” was related to the patients or specimens while “I” referred to the methods of analyses. The major parameters were the thickness and types of zirconia. The correlation with light curing parameters was established such as light transmittance, intensity, and exposure time in clinical situations. Data of the reports were harvested directly into a single data-collection form to avoid multiple data record in the case of multiple reports in the same study (e.g., reports with different set-ups).

3.Results

The literature search identified a total of 163 articles in PubMed, as shown in Figure 1. Duplicates were removed and then titles and abstracts of 137 articles were independently evaluated by two authors. A number of 114 articles were excluded because they did not meet the inclusion criteria. The remaining 23 potentially relevant studies were then evaluated (Fig. 1). Of those studies, 2 were excluded because they did not provide comprehensive data considering the purpose of the present study. Thus 21 studies were included in this review [8, 9, 22, 26, 27, 32–38, 10, 39, 40, 13–15, 18–21].

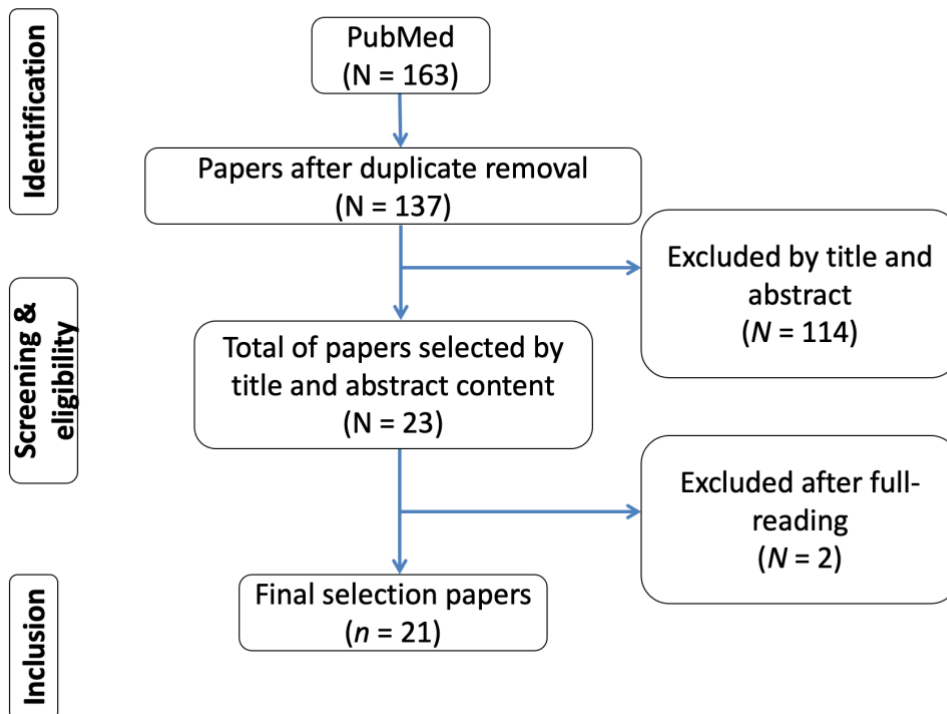


Figure 1. Flow diagram of the search strategy used in this study.

Of the 21 studies selected, 9 (42.9%) investigated the light-curing effect while five other articles (23.8%) evaluated the ceramic translucency. Three studies (14.3%) evaluated the degree of conversion of the resin-matrix cement and then four articles (19%)

assessed the veneer thickness. The retrieved data on the resin-matrix cement, zirconia veneer thickness, the light curing, degree of conversion, and microhardness are given in Table 1. The major findings are drawn as follow:

- The amount of light that passes through the zirconia structure depends on the translucency, microstructure, zirconia composition, irradiation energy, thickness, porosity, and manufacturing technique. Indeed, fully stabilized zirconia (FSZ) is more translucent than partially stabilized zirconia (PSZ) [9, 20, 21, 33];
- The translucency of the restoration is affected by the zirconia thickness and by the resin-matrix cement. A high translucency is achieved within thin zirconia veneer associated with translucent zirconia and resin-matrix cement. The highest light transmittance was recorded through the zirconia (Ceramil Zi, DD BIO ZM translucent, ZENOSTAR, Prettau, Ceramill Zolid, InCoris TZI) thickness up to 0.3 mm. A lower light irradiance was recorded on zirconia with thickness from 0.5 mm and in colored zirconia veneer when compared to translucent zirconia veneer [18, 19, 35, 36];
- The degree of conversion of the resin-matrix cements is strongly affected by the polymerization mode and the zirconia thickness. Thus, an increase in veneer thickness from 0.1 mm (ultra-thin veneer) up to 1.5 mm decrease the light transmission through the zirconia to the resin-matrix cement causing a negative effect on the degree of conversion of the resin-matrix cement [14, 15, 27]. For instance, the degree of conversion ranged from 40% to 50% after 5 min from light-curing and increased gradually to 70% to 80% one week after light-curing [14, 15, 27];

- The highest degree of conversion was recorded for dual-curing resin cements as a function of the polymerization reaction of the resin-matrix cement [14]. An adequate degree of conversion of the resin-matrix cement can be achieved on a proper intensity of the light-curing unit source at 1400 mW/cm² and exposure time ranging from 20 up to 120 s. Also, the degree of conversion of the resin-matrix cement can occur through zirconia with 1mm thickness on 1000 mW/cm² irradiation for 60 s [39]. Authors recommend the use of dual-curing resin cements but with a lower light sensitivity [8]. Also, the wavelength of the light-curing unit should be at the blue light range (360–540 nm) to stimulate all the potential photoinitiators in the resin-matrix phase since current resin-matrix cements can have different photoinitiator molecules;
- The decrease in microhardness values recorded on the resin-matrix cement was resultant from the low degree of conversion due to an increase in veneer thickness [10, 13, 26].

4. Discussion

The present integrative review described the major results of relevant previous studies taking into account the effect of the zirconia veneer thickness on the light transmission and degree of conversion of resin-matrix cements during light curing. The microstructure, translucency, and thickness of zirconia veneers do affect the light transmission to the resin-matrix cement. Also, the type of resin-matrix cement and light-curing method are determinant on the polymerization and properties of the resin-matrix cement. Thus, the findings validate the hypothesis of this study. A detailed discussion

on the main factors affecting the light-curing of resin cements through zirconia veneer is provided as follow.

4. 1. Zirconia: microstructure, translucency, and thickness

YTZP has been used to manufacture prosthetic structures such as esthetic veneers and single-unit (crown) or multi-unit prostheses due to their physicochemical properties [1, 2]. The fracture toughness of YTZP is around 9-10 MPa.m^{1/2} while the 3-point bending strength is ranging from 900 up to 1200 MPa [1, 17]. The first type of ordinary zirconia was stabilized with 3mol% yttria (3Y-TZP) although the opacity is too high to mimic the teeth enamel structure. However, the 3Y-TZP polycrystalline microstructure results in a low translucency and therefore, the thickness of the material affects the curing process of resin-matrix cements. Translucent ceramic or glass-ceramics are required to mimic the optical properties of teeth enamel as seen in Figure 2. Changes in the chemical composition of zirconia resulted in high translucency zirconia that has given the capability to manufacture the entire prosthetic crown structure [8, 13]. In this way, the percentage of yttria has been increased from 5 up to 8% Y₂O₃ and therefore the cubic crystals were added ranging from 20 up to 50% in the microstructure, that resulted in the translucency increase but some disadvantages are related to the mechanical properties [1, 2]. Therefore, the zirconia type for ultra-thin veneers should be produced from tetragonal zirconia partially stabilized by yttria (3Y-TZP) with high crystalline-content to provide translucency. Another way to increase the zirconia translucency was to decrease the amount of alumina (0.05%) and increasing the content of lanthanum oxide (0.2%). Also, the size of crystals was decreased below 80 nm to enhance the translucence of the zirconia [1, 2, 17]. Also, a decrease in the size of crystals can control

a roughness of the inner surface for cementation and therefore a low roughness provides a low light scattering leading to a proper light transmission to the resin cement [20, 41]. Thus, the surface treatment of the inner surface of the zirconia veneer must consider an adequate roughness avoiding producing an opaque material.

The optical state between complete opacity and transparency named translucency is the essential factor in proper selection of ceramic materials to achieve required aesthetic outcomes. The selection of the zirconia type is critical to the recommended translucency for enamel or dentin. Also, porosity, oxide additives, grain size, and thickness control the dispersion and absorption of light during the polymerization of prosthetic cementation [13, 18, 21]. Absolute translucency can be measured by the percentage of the transmitted light. The “relative translucency” is recorded using either the contrast ratio or the translucency parameter (TP), which are calculated as difference in luminance and respectively, color, when the material is assessed upon ideal black in function with the white background [18, 33]. Opaque materials reveal high TP values. The contrast ratio is defined as the illuminance ratio (Y) of the test material when placed over a black background (Y_b) or a white background (Y_w) [18, 33]. However, ideal white and black backgrounds are not commonly used for translucency measurements, due to their availability. A relative translucency parameter (RTP) must be considered when optical measurements are carried out on non-ideal backgrounds and when optical properties of the material are not homogeneous throughout its thickness. The values of this parameter are relative to the color of the white and black backgrounds used for measurements [2, 12, 18, 33].

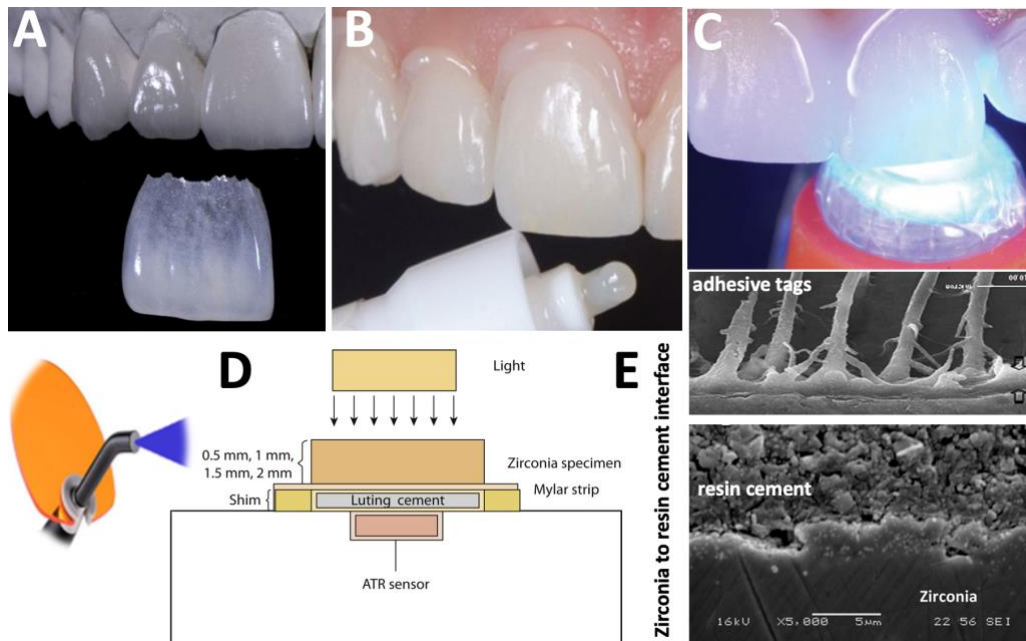


Figure 2. Schematics of the resin-matrix cement light curing through a zirconia veneer. (A) Zirconia veneer and the (B) resin-matrix cement application. (C) Light-curing of the resin-matrix cement. (D) Schematics of the *in vitro* tests assessing the effect of different thickness of zirconia veneer (Adapted from Sulaiman et al [26]). (E) SEM images of the zirconia to resin-matrix cement.

Prior the cementation, Y-TZP inner surface is modified by airborne abrasion (grit-blasting process) with alumina (Al_2O_3) particles followed by silica (SiO_2) particles [4–6]. Also, the application of a glass-ceramic thin layer (liner) can be an alternative approach to provide a silica-based coating which can be conditioned by 9% hydrofluoric acid (HF) [42]. However, the increase in roughness can also act as factor of light diffraction depending on roughness magnitude.

Regarding the low translucency and properties of 3YTZP, the thickness can play a key role on the clinical success of prosthetic restoration concerning cementation, esthetics, and mechanical performance. The selected studies have shown a significant influence

of the veneer thickness on the light transmission through the ceramic and polymerization of the resin-matrix cement, as seen in Table 1. The minimum ceramic thickness for monolithic indirect restorations was recorded at around 0.2-0.3 mm. A previous study reported 46.5% contrast ratio and 8.6% higher translucency for 0.3 mm Y-TZP veneer when compared to 0.5 mm YTZP veneer [40]. The findings were corroborated by another previous study on the measurement of the light irradiance by Raman light spectrometry for 40 s regarding different thickness of zirconia veneers [30]. In fact, there is an inverse relationship between irradiating energy, translucency, and thickness; since a thick or opaque zirconia veneer can decrease the light transmission to the resin cement while. [26].

4.2. Resin-matrix cements and light-curing parameters

Considering the chemical similarity to resin-based composite materials, the chemical composition of resin-matrix cements involves several monomers and fillers, as shown in Table 1. The polymer-matrix of resin cements is composed of methacrylate monomers (40-60%wt) like Bis-GMA, UEDMA, and TEGDMA while the inorganic content is composed of colloidal silica, ytterbium fluoride, or barium glass fillers [38, 43]. Taking into account the chemical composition, resin-matrix cements have properties quite similar to that of flowable resin composite materials such as: low solubility, translucency, and flowability [10, 24, 43]. The viscosity or flowability of the resin-matrix cements provide a mechanical interlocking to the primer-coated enamel and restorative surfaces. Also, the presence of 10-Methacryloyloxydecyl dihydrogen phosphate (10-MDP) promotes a physicochemical bonding to restorative ceramic surfaces [24]. With the advances in adhesive dentistry, resin-matrix cements have become the first choice

materials for the adhesion of ceramics to the teeth surfaces due to their physicochemical properties and clinical procedures [13, 24, 38].

The chemical composition of the resin-cements also varies in the presence or not of photoinitiator compounds. Currently, dual curing resin-matrix cements are the most commonly materials used in fixed prostheses, since they have a polymerization activated by visible light at around 320-480 nm and by a chemical polymerization activation when two pastes are mixed [14, 15, 27]. The interaction between the benzoyl peroxide and tertiary amines (dimethyl-p-toluidine) is responsible for the chemical activation while photo-initiators such as canforquinone are stimulated by the light. The adequate properties of the materials are achieved by the accomplishment of the polymerization process that is mainly dependent on the chemical composition of the material and veneer material features [26, 27, 37]. Considering the chemical composition of the resin-matrix cements, most of the studies have correlate the chemical composition to the light irradiance time and intensity by infra-red spectroscopy analyses [26, 27, 37]. Also, the content and optical properties of the fillers can affect the light transmittance. On the other hand, a high filler content provides mechanical strength to the material [15, 38].

A previous study reported a negative effect of the Y-TZP thickness on the polymerization of resin-matrix cements [21] that was related to an inadequate irradiance of the light source. A decrease of light curing transmission source was recorded from 900 mW/cm² (without veneer) down to 585 mW/cm² through 0.2 mm polycrystalline ceramic and to 549 mW/cm² through 1.2 mm ceramic polycrystalline ceramic. In fact, dual resin cement showed significant differences in polymerization under polycrystalline ceramic thickness of 1.2 mm when compared to veneer thicknesses ranging from 0.3 to 0.9 mm. The

analyses were performed with a spectrophotometer at the middle and cervical regions across the veneer. The values recorded for contrast ratio and translucency were acceptable at the body region although there was a bias of results for the cervical region. On 1.65 mm veneers, the degree of conversion of the resin-matrix cement was significantly low when the light irradiation was below 300 mW.cm⁻². However, the threshold thickness of Y-TZP veneer was not determined [21]. Previous studies evaluated the polymerization of the resin-matrix cement through different Y-TZP specimens, as follow: 0.5-3, 0.6-1.0, 1.5, and 0.5-1.5 mm. The highest mean values of microhardness and degree of conversion were recorded for 0.5-1.0 mm YTZP thickness, as seen in Table 1 [21, 22, 35, 36]. Kim et al. [14], Gultekim et al. [22], and Inokoshi et al. [36], showed that the transmittance of light decreases as the thickness of the ceramic veneer increases, generating an inadequate light transmission and poor degree of conversion in the inner region of the prosthetic restoration [15]. A thick 3YTZP veneer negatively affects the light irradiance and polymerization of the resin-matrix cement and then decreases its degree of conversion and color stability [21, 36]. Additionally, monolithic Y-TZP provided a lower light transmission value compared to other ceramic materials like lithium disilicate reinforced glass-ceramic [12].

The light-curing process depends on the irradiance source, exposure time, and distance, and therefore on the resin-matrix cement [47-49]. Thus, the degree of conversion related to the light-curing is a key factor when selecting resin-matrix composite materials [24, 25]. A low degree of conversion can promote detrimental effects to the physicochemical properties of the resin-matrix materials such as water sorption, solubility, strength, hardness, and optical properties [38]. Also, that compromise the tooth-cement-zirconia interface. Resin-matrix cements have been evaluated by several

factors concerning physical properties like hardness, elastic modulus, and strength, as seen in Table 1 [15, 21]. The depth of the light-curing irradiance can be related to both resin-matrix composite thickness and distance from the light-curing handheld device tip [13, 27]. Previous studies reported an enhancement of the degree of conversion and microhardness of the resin-matrix composite when the irradiance time was increased [10, 15]. High values of degree of conversion and micro-hardness were recorded for resin-matrix cements after LED irradiation time ranging from 20 up to 120 s, as shown in Table 1. According to the results of similar studies, dual curing resin-matrix cements have revealed greater success when compared to self-curing or light curing cements [15]. The degree of conversion of four brands of resin-matrix cements has been evaluated by ATR/FTIR spectrometry, while the mechanical behavior has been evaluated by dynamic indentation test (e.g., microhardness test) [27]. Lopes et al. [27], showed that the chemical curing has a low microhardness value and therefore the finding was also corroborated by another previous study [18]. The groups of resin-matrix cements that were light-cured through zirconia or lithium disilicate glass-ceramic veneers showed a higher degree of conversion than those for self-cured groups [37]. Therefore, a previous study revealed higher values of VHN (Vickers Hardness Number) for samples light-cured under LED source when compared to QTH source at higher depth of light-curing [22].

An important aspect of the light-curing parameters is the power that the light source presents during polymerization procedure of the restorations. Irradiation power, wavelength, and curing time determine the energy for polymerization of the material. Another key factor to take into account is the photoinitiation molecules in the material, that generate the activation of free radicals [27, 37]. Most of the studies carried out the

light curing with a wavelength at 430-480 nm [19, 21, 22, 26, 35, 36] although a few studies reported optimal values of degree of conversion and microhardness by using a wavelength at 500 nm (Fig. 2) [14, 22, 26]. One study showed that the highest transmitted irradiance was achieved through a 0.5 mm ceramic thickness regardless of the type of material, although it was decreasing as the ceramic thickness increased. This study evaluated 35 samples of zirconia and 7 of glass ceramics (control), which were then stained with different shades (CL1, CL2, CL3 and CL4) but one sample remained unstained (CL0) [8].

Among the retrieved articles, the highest power values of the light curing sources recorded as regards the depth of the polymerization were at 1400 and 1500 nW/cm² [15, 18]. In fact, previous studies recommended a light intensity higher than 1000 nW/cm² for polymerization of resin-matrix cements [19, 21, 22, 26, 35, 36]. However, adequate degree of conversion of dual curing resin-matrix cements was achieved under LED light-curing in a lower power of 718 nW/cm² [37]. A previous study showed that all groups had a higher degree of conversion, when they had been exposed to a longer irradiation time. Nevertheless, there was no significant difference for the irradiated groups with 1000 mW/cm² and 1500 mW/cm². On longer exposure time, an increase in temperature can be noted for 1000 mW/cm² when compared with an irradiation of 500 mW/cm² that can lead unfavorable damage of the dentin tissue [39]. The increased energy absorbed by the dentin surface can promote the denaturation of proteins and the damage of dentinoblasts leading to a harmful sensitivity to the patients. The damage of the dentin-pulp complex depends on the level and depth of injury. Furthermore, such damage can be irreversible resulting in the re-treatment by using invasive procedures and the replacement of the restoration. A previous study assessed the irradiation

technique, polymerization time, and storage conditions by measuring the, Vickers hardness and the degree of conversion of resin-matrix cement. Findings revealed that proper mechanical properties can be achieved within a minimum irradiation time of 20 s [43].

In fact, dual polymerization of resin-matrix cements is recommended since the light-curing unit and parameters might have limitations regarding and thickness and microstructure of different zirconia structures. Knowledge on visible and blue light could help clinicians to individually adapt the light curing parameters to different ceramic materials. Also, the light-curing unit can have different light wavelength and intensity for several resin-matrix cements regarding the development of several photoinitiators for the polymeric matrix of the resin cement. On the other hand, the technicians must provide the maximum information on the microstructure of the zirconia veneer for adjustment of the light curing guidelines. Further studies should be carried out concerning the chemical composition, thickness, and microstructure (i.e., crystal size, crystallinity, defects) of zirconia-based materials. Also, surface modifications of the inner surface of zirconia veneer or glass-ceramic coating of the outer region can affect the light transmission through the ceramic material towards to resin-matrix cement and therefore those factors should be carefully evaluated in future studies.

5. Conclusions

This integrative review reported previous findings regarding the effect of the thickness and microstructure of zirconia on the light transmission for the activation of the resin-matrix cements. Within the limitations of the selected studies, the following conclusions can be drawn:

- The thickness of the zirconia veneers is determinant for an appropriate esthetic outcome since a thick the zirconia-based veneer negatively affected the light transmitted to the resin-matrix cement. That results in the decrease of the degree of conversion of the resin-matrix monomers leading to a low chemical stability which can be detected by color instability and low microhardness values;
- The zirconia microstructure also play an important role on the light transmission once the polycrystalline structure can vary depending on the chemical composition and sintering of the zirconia structure by different manufacturers. However, zirconia materials such as Y-TZP containing lower amounts of alumina showed higher transmittance;
- In clinical applications, the light-curing parameters should also be controlled regarding the thickness and microstructure of zirconia structures. For instance, the light-curing intensity and time should be increased for thick and opaque zirconia. In this way, thin and ultra-thin zirconia veneers associated with translucent resin-matrix cements have achieved proper optical results for clinical applications as esthetic veneers.

Compliance with Ethical Standards

Conflict of Interest: The authors, namely Christie Tafur-Zelada, Oscar Carvalho, Bruno Henriques, Filipe Silva, Mutlu Özcan, & Júlio Souza, declare that they have no conflict of interest.

Funding: This work was supported by FCT-Portugal [UID/EEA/04436/2013, NORTE-01-0145-FEDER- 000018], HAMaBICo and Project LaserMULTICER [POCI-01-0145-FEDER-031035].

Ethical approval: This article does not contain any studies with human participants or animals performed by any of the authors

Informed consent: For this type of study, formal consent is not required.

References

1. Zhang Y, Lawn BR (2018) Novel Zirconia Materials in Dentistry. *J Dent Res* 97:140–147. <https://doi.org/10.1177/0022034517737483>
2. Lümke N, Pfefferle R, Jerman E, et al (2020) Translucency, flexural strength, fracture toughness, fracture load of 3-unit FDPs, Martens hardness parameter and grain size of 3Y-TZP materials. *Dent Mater* 36:838–845. <https://doi.org/10.1016/j.dental.2020.03.027>
3. Stawarczyk B, Frevert K, Ender A, et al (2016) Comparison of four monolithic zirconia materials with conventional ones: Contrast ratio, grain size, four-point flexural strength and two-body wear. *J Mech Behav Biomed Mater* 59:128–138. <https://doi.org/10.1016/j.jmbbm.2015.11.040>
4. Egilmez F, Ergun G, Cekic-Nagas I, et al (2013) Effect of surface modification on the bond strength between zirconia and resin cement. *J Prosthodont Off J Am Coll Prosthodont* 22:529–536. <https://doi.org/10.1111/jopr.12030>
5. Pereira L de L, Campos F, Dal Piva AM de O, et al (2015) Can application of universal primers alone be a substitute for airborne-particle abrasion to improve adhesion of resin cement to zirconia? *J Adhes Dent* 17:169–174. <https://doi.org/10.3290/j.jad.a33974>

6. Henriques B, Fabris D, Tuyama E, et al (2019) Shear bond strength of PEEK and PEEK-30GF cemented to zirconia or titanium substrates. *J Adhes Sci Technol* 33:1090–1101. <https://doi.org/10.1080/01694243.2019.1565289>
7. Özcan M, Bernasconi M (2015) Adhesion to zirconia used for dental restorations: a systematic review and meta-analysis. *J Adhes Dent* 17:7–26. <https://doi.org/10.3290/j.jad.a33525>
8. Ilie N, Stawarczyk B (2014) Quantification of the amount of light passing through zirconia: the effect of material shade, thickness, and curing conditions. *J Dent* 42:684–690. <https://doi.org/10.1016/j.jdent.2014.03.007>
9. Tribst JPM, Dal Piva AM de O, Penteado MM, et al (2018) Influence of ceramic material, thickness of restoration and cement layer on stress distribution of occlusal veneers. *Braz Oral Res* 32:e118. <https://doi.org/10.1590/1807-3107bor-2018.vol32.0118>
10. Turp V, Ongul D, Gultekin P, et al (2015) Polymerization efficiency of two dual-cure cements through dental ceramics. *J Istanbul Univ Fac Dent* 49:10–18. <https://doi.org/10.17096/jiufd.25575>
11. Ioannidis A, Muhlemann S, Ozcan M, et al (2019) Ultra-thin occlusal veneers bonded to enamel and made of ceramic or hybrid materials exhibit load-bearing capacities not different from conventional restorations. *J Mech Behav Biomed Mater* 90:433–440. <https://doi.org/10.1016/j.jmbbm.2018.09.041>
12. Harada K, Raigrodski AJ, Chung K-H, et al (2016) A comparative evaluation of the translucency of zirconias and lithium disilicate for monolithic restorations. *J Prosthet Dent* 116:257–263. <https://doi.org/10.1016/j.prosdent.2015.11.019>
13. Turp V, Sen D, Poyrazoglu E, et al (2011) Influence of zirconia base and shade

- difference on polymerization efficiency of dual-cure resin cement. J Prosthodont Off J Am Coll Prosthodont 20:361–365.
<https://doi.org/10.1111/j.1532-849X.2011.00721.x>
14. Kim M-J, Kim K-H, Kim Y-K, Kwon T-Y (2013) Degree of conversion of two dual-cured resin cements light-irradiated through zirconia ceramic disks. J Adv Prosthodont 5:464–470. <https://doi.org/10.4047/jap.2013.5.4.464>
 15. Alovisi M, Scotti N, Comba A, et al (2018) Influence of polymerization time on properties of dual-curing cements in combination with high translucency monolithic zirconia. J Prosthodont Res 62:468–472.
<https://doi.org/10.1016/j.jpor.2018.06.003>
 16. Guazzato M, Albakry M, Ringer SP, Swain M V (2010) Strength , fracture toughness and microstructure of a selection of all-ceramic materials . Part I . Pressable and alumina glass-infiltrated ceramics. Dent Mater 20:441–448
 17. Guazzato M, Albakry M, Ringer SP, Swain M V. (2004) Strength, fracture toughness and microstructure of a selection of all-ceramic materials. Part I. Pressable and alumina glass-infiltrated ceramics. Dent Mater 20:441–448.
<https://doi.org/10.1016/j.dental.2003.05.003>
 18. Caprak YO, Turkoglu P, Akgungor G (2019) Does the Translucency of Novel Monolithic CAD/CAM Materials Affect Resin Cement Polymerization with Different Curing Modes? J Prosthodont Off J Am Coll Prosthodont 28:e572–e579. <https://doi.org/10.1111/jopr.12956>
 19. Capa N, Celebi C, Casur A, et al (2017) The translucency effect of different colored resin cements used with zirconia core and titanium abutments. Niger J Clin Pract 20:1517–1521. https://doi.org/10.4103/njcp.njcp_160_17

20. Sulaiman TA, Abdulmajeed AA, Donovan TE, et al (2015) Optical properties and light irradiance of monolithic zirconia at variable thicknesses. *Dent Mater* 31:1180–1187. <https://doi.org/10.1016/j.dental.2015.06.016>
21. Turp V, Turkoglu P, Sen D (2018) Influence of monolithic lithium disilicate and zirconia thickness on polymerization efficiency of dual-cure resin cements. *J Esthet Restor Dent Off Publ Am Acad Esthet Dent* . [et al] 30:360–368. <https://doi.org/10.1111/jerd.12390>
22. Gultekin P, Pak Tunc E, Ongul D, et al (2015) Curing efficiency of dual-cure resin cement under zirconia with two different light curing units. *J Istanbul Univ Fac Dent* 49:8–16. <https://doi.org/10.17096/jiufd.97059>
23. Paes PNG, Bastian FL, Jardim PM (2017) The influence of Y-TZP surface treatment on topography and ceramic/resin cement interfacial fracture toughness. *Dent Mater* 33:976–989. <https://doi.org/10.1016/j.dental.2017.06.004>
24. Thompson JY, Stoner BR, Piascik JR, Smith R (2011) Adhesion/cementation to zirconia and other non-silicate ceramics: where are we now? *Dent Mater* 27:71–82. <https://doi.org/10.1016/j.dental.2010.10.022>
25. Vrochari AD, Eliades G, Hellwig E, Wrbas K-T (2009) Curing efficiency of four self-etching, self-adhesive resin cements. *Dent Mater* 25:1104–1108. <https://doi.org/10.1016/j.dental.2009.02.015>
26. Sulaiman TA, Abdulmajeed AA, Donovan TE, et al (2015) Degree of conversion of dual-polymerizing cements light polymerized through monolithic zirconia of different thicknesses and types. *J Prosthet Dent* 114:103–108. <https://doi.org/https://doi.org/10.1016/j.prosdent.2015.02.007>

27. Lopes C de CA, Rodrigues RB, Silva ALFE, et al (2015) Degree of Conversion and Mechanical Properties of Resin Cements Cured Through Different All-Ceramic Systems. *Braz Dent J* 26:484–489. <https://doi.org/10.1590/0103-6440201300180>
28. De Souza G, Braga RR, Cesar PF, Lopes GC (2015) Correlation between clinical performance and degree of conversion of resin cements: a literature review. *J Appl Oral Sci* 23:358–368. <https://doi.org/10.1590/1678-775720140524>
29. Noronha Oliveira M, Schunemann WVH, Mathew MT, et al (2018) Can degradation products released from dental implants affect peri-implant tissues? *J Periodontal Res* 53:1–11. <https://doi.org/10.1111/jre.12479>
30. Souza JCM, Sordi MB, Kanazawa M, et al (2019) Nano-scale modification of titanium implant surfaces to enhance osseointegration. *Acta Biomater.* 94:112–131
31. Schünemann FH, Galárraga-Vinueza ME, Magini R, et al (2019) Zirconia surface modifications for implant dentistry. *Mater Sci Eng C* 98:1294–1305. [https://doi.org/https://doi.org/10.1016/j.msec.2019.01.062](https://doi.org/10.1016/j.msec.2019.01.062)
32. Jung H, Friedl K-H, Hiller K-A, et al (2006) Polymerization efficiency of different photocuring units through ceramic discs. *Oper Dent* 31:68–77. <https://doi.org/10.2341/04-188>
33. Bansal R, Taneja S, Kumari M (2016) Effect of ceramic type, thickness, and time of irradiation on degree of polymerization of dual - cure resin cement. *J Conserv Dent* 19:414–418. <https://doi.org/10.4103/0972-0707.190010>
34. Shiomuki D, Minami H, Tanaka T, Suzuki S (2013) Influence of light irradiation on Vickers hardness of dual-cure cement polymerized under restorations. *Dent*

- Mater J 32:449–455. <https://doi.org/10.4012/dmj.2012-306>
35. Malkondu O, Tinastepe N, Kazazoglu E (2016) Influence of type of cement on the color and translucency of monolithic zirconia. *J Prosthet Dent* 116:902–908. <https://doi.org/10.1016/j.prosdent.2016.05.001>
 36. Inokoshi M, Pongprueksa P, De Munck J, et al (2016) Influence of Light Irradiation Through Zirconia on the Degree of Conversion of Composite Cements. *J Adhes Dent* 18:161–171. <https://doi.org/10.3290/j.jad.a35842>
 37. Shim JS, Kang JK, Jha N, Ryu JJ (2017) Polymerization Mode of Self-Adhesive, Dual-Cured Dental Resin Cements Light Cured Through Various Restorative Materials. *J Esthet Restor Dent Off Publ Am Acad Esthet Dent* . [et al] 29:209–214. <https://doi.org/10.1111/jerd.12285>
 38. Valentino TA, Borges GA, Borges LH, et al (2010) Dual resin cement knoop hardness after different activation modes through dental ceramics. *Braz Dent J* 21:104–110. <https://doi.org/10.1590/s0103-64402010000200003>
 39. Shim JS, Han SH, Jha N, et al (2018) Effect of Irradiance and Exposure Duration on Temperature and Degree of Conversion of Dual-Cure Resin Cement for Ceramic Restorations. *Oper Dent* 43:E280–E287. <https://doi.org/10.2341/17-283-L>
 40. Kumagai N, Hirayama H, Finkelman MD, Ishikawa-Nagai S (2013) The effect of translucency of Y-TZP based all-ceramic crowns fabricated with difference substructure designs. *J Dent* 41 Suppl 3:e87-92. <https://doi.org/10.1016/j.jdent.2012.10.005>
 41. Akar GC, Pekkan G, Cal E, et al (2014) Effects of surface-finishing protocols on the roughness, color change, and translucency of different ceramic systems. *J*

- Prosthet Dent 112:314–321. <https://doi.org/10.1016/j.prosdent.2013.09.033>
42. Pozzobon JL, Pereira GKR, Wandscher VF, et al (2017) Mechanical behavior of yttria-stabilized tetragonal zirconia polycrystalline ceramic after different zirconia surface treatments. Mater Sci Eng C Mater Biol Appl 77:828–835. <https://doi.org/10.1016/j.msec.2017.03.299>
43. Ilie N, Bauer H, Draenert M, Hickel R (2013) Resin-based composite light-cured properties assessed by laboratory standards and simulated clinical conditions. Oper Dent 38:159–167. <https://doi.org/10.2341/12-084-L>