



Year: 2012

Analysis of hydrolyzable polyethylene glycol hydrogels and deproteinized bone mineral as delivery systems for glycosylated and non-glycosylated bone morphogenetic protein-2

Hänseler, P ; Jung, U W ; Jung, R E ; Choi, K ; Choi, K S ; Hämmerle, C H F ; Weber, Franz E

Abstract: Bone morphogenetic proteins (BMP), in particular BMP-2, are the growth factors primarily responsible for osteoinduction. A knowledge of interactions between bone substitute materials and growth factor variants is crucial to designing bone substitutes with an ideal release profile. Here we compare glycosylated and non-glycosylated recombinant human bone morphogenetic protein-2 (rhBMP-2) either incorporated into a hydrolyzable polyethylene glycol (PEG) hydrogel developed as a slow release system or adsorbed to a deproteinized bovine bone matrix (DBBM), a clinically well-established bone substitute material. rhBMP-2 loaded materials were immersed in cell culture medium and rhBMP-2 concentration profiles in the supernatant were determined by an enzyme-linked immunosorbent assay. The corresponding biological activities were assessed in vitro by alkaline phosphatase activity assay. We show a strong affinity of rhBMP-2 for DBBM and reduced biological activity after its release from PEG hydrogels. Glycosylated rhBMP-2 was significantly less affected by the hydrogel and interacted significantly more strongly with DBBM than non-glycosylated rhBMP-2. We therefore question the combination of PEG hydrogels with DBBM as a rhBMP-2 delivery system over DBBM alone, since rhBMP-2 released from the hydrogel will be trapped by DBBM. Moreover, our results suggest that glycosylated rhBMP-2 is favorable in combination with PEG hydrogels, since its activity is better preserved, whereas in combination with DBBM non-glycosylated rhBMP-2 is favorable, benefiting from an initially higher concentration of free rhBMP-2.

DOI: <https://doi.org/10.1016/j.actbio.2011.08.002>

Posted at the Zurich Open Repository and Archive, University of Zurich

ZORA URL: <https://doi.org/10.5167/uzh-62945>

Journal Article

Accepted Version

Originally published at:

Hänseler, P; Jung, U W; Jung, R E; Choi, K; Choi, K S; Hämmerle, C H F; Weber, Franz E (2012). Analysis of hydrolyzable polyethylene glycol hydrogels and deproteinized bone mineral as delivery systems for glycosylated and non-glycosylated bone morphogenetic protein-2. *Acta Biomaterialia*, 8(1):116-123.

DOI: <https://doi.org/10.1016/j.actbio.2011.08.002>

Analysis of Hydrolyzable Polyethylene Glycol Hydrogels and Deproteinized Bone Mineral as Delivery Systems for Glycosylated and Non-glycosylated Bone Morphogenetic Protein-2

Patrick Hänseler^a

Ui-Won Jung^c

Ronald E. Jung^b

Kyoung-Hee Choi^d

Kyoo-Sung Cho^c

Christoph H. F. Hämmerle^b

Franz E. Weber^a

Running Title

E. coli-expressed rhBMP-2 release

^aOral Biotechnology & Bioengineering, Department of Cranio-Maxillofacial Surgery, University Hospital Zurich, Zurich, Switzerland

^cDepartment of Periodontology, Research Institute for Periodontal Regeneration, College of Dentistry, Yonsei University, Seoul, Korea.

^dResearch Development Institute, Cowellmedi Co. LTD.

^bDepartment of Fixed and Removable Prosthodontics and Dental Material Science, Dental School, University of Zurich, Switzerland

Correspondence:

FE Weber, University Hospital; Dept. of Cranio-Maxillofacial Surgery, Oral Biotechnology & Bioengineering; Frauenklinikstrasse 24, 8091 Zürich; Switzerland
Tel: +41 44 255 5055, Fax: +41 44 255 4179; Email: franz.weber@zzm.uzh.ch

ABSTRACT

Bone morphogenetic proteins (BMPs), in particular BMP-2, are the growth factors primarily responsible for osteoinduction. Knowledge of interactions between bone substitute materials and growth factor variants is crucial for designing bone substitutes with an ideal release profile. Here we compare glycosylated and non-glycosylated recombinant human bone morphogenetic protein-2 (rhBMP-2) either incorporated into a hydrolyzable polyethylene glycol (PEG) hydrogel developed as a slow release system or adsorbed to a deproteinized bovine bone matrix (DBBM), a clinically well-established bone substitute material. rhBMP-2 loaded materials were immersed in cell culture medium and rhBMP-2 concentration profiles in the supernatant were determined by an enzyme-linked immunosorbent assay (ELISA). The corresponding biological activities were assessed *in vitro* by an alkaline phosphatase activity assay. We show a strong affinity of rhBMP-2 to DBBM and a reduced biological activity after its release from PEG hydrogels. Glycosylated rhBMP-2 was significantly less affected by hydrogels and interacted significantly stronger with DBBM than non-glycosylated rhBMP-2. We therefore question the combination of PEG hydrogels with DBBM as a rhBMP-2 delivery system over DBBM alone since rhBMP-2 released from the hydrogel will be trapped by DBBM. Moreover, our results suggest that glycosylated rhBMP-2 is favorable in combination with PEG hydrogels since its activity is better preserved. Whereas in combination with DBBM, non-glycosylated rhBMP-2 is favorable in order to benefit from an initially higher concentration of free rhBMP-2.

Key words:

bone substitutes; rhBMP-2 protein, recombinant; hydrogel; Bio-Oss; drug delivery system, glycosylated versus non-glycosylated protein

1 Introduction

Bone has a unique capacity to heal itself without leaving a scar [1]. However, if a gap derived from an injury, disease or a surgical treatment reaches a critical size, the body is not able to repair the void on its own. For these critical-sized defects or when bone augmentation is required, a bone substitute is needed. The ideal material for a bone substitute provides a three-dimensional, mechanically stable structure, serves as a carrier for growth factors that enhance bone in-growth, contains living osteoblastic cells that are accepted by the body and should eventually be replaced by newly formed bone [2-4]. Autologous bone fulfills all of these criteria. Unfortunately, its use has severe drawbacks, namely increased morbidity at the harvest site and limited supply [5]. Therefore, alternatives such as allografts, xenografts or alloplasts are used. However, none of them provide all the properties of autografts [6].

Deproteinized bovine bone matrix (DBBM) is the gold standard off-the-shelf bone substitute material in dentistry [7]. It consists of the mineral phase of bovine bone, containing hydroxyapatite as the main component. DBBM is devoid of any organic material, therefore it is not as tough as natural bone and devoid of bone-inducing growth factors [8], making its combination with bone-inducing growth factors advantageous [9].

Bone morphogenetic proteins (BMPs), in particular BMP-2 and BMP-7, are the growth factors mainly responsible for osteoinduction [10]. They recruit and stimulate adult mesenchymal stem cells and preosteoblastic cells to migrate, proliferate and mature into osteoblasts [11, 12]. Currently, glycosylated Chinese hamster ovary (CHO)-expressed recombinant human BMP-2 (rhBMP-2) in combination with a collagen carrier (Infuse®, Medtronic Sofamor Danek, Memphis, Tennessee) is

commercially available and approved by the Food and Drug Administration (FDA) and the European authorities for lumbar spine fusion and persisting long bone defects. Glycosylated rhBMP-2 is also approved for several dental applications [13]. Non-glycosylated rhBMP-2 produced by the prokaryotic expression system using *E. coli*, is an alternative that could substantially reduce production cost and the price for clinical application. Despite the fact that *E. coli*-derived proteins are non-glycosylated, the biological potential of non-glycosylated rhBMP-2 has been reported to have bone-inducing activity similar to the glycosylated form [14-17]. In a human clinical trial, we demonstrated the efficacy of non-glycosylated rhBMP-2 in a bone augmentation procedure [9].

Controlling the release profile of rhBMP-2 from carrier materials is crucial to deliver the minimal effective growth factor load needed for bone reconstruction. Analysis of BMP expression during fracture healing revealed that BMP-2 expression was upregulated early and was elevated for up to 30 days [18]. It is therefore of advantage to release rhBMP-2 over a time period of days to weeks rather than hours [19]. Rapid diffusion away from the implantation site into body fluids, premature degradation of the carrier material, and inactivation of rhBMP-2 due to unwanted interactions with the carrier materials may limit the effectiveness of rhBMP-2 [19-24]. An approach for a system composed of clinically evaluated materials that provides mechanical stability and allows sustained growth factor delivery is the combination of DBBM with hydrolysable polyethylene glycol (PEG) hydrogels [25-30]. In such a system, the release profile of the growth factor is dependent on the physical binding strength to the hydrogel, the degradation characteristics of the hydrogel and the interaction of the applied growth factor with the DBBM. A tunable, hydrolysable PEG hydrogel system based on a Michael-type reaction between PEG chains

functionalized with acrylate groups and thiol groups has been previously developed [31]. The PEG system has been evaluated in clinical studies [32] and it was recently demonstrated that improved bone formation can be achieved by entrapping rhBMP-2 as well as parathyroid hormone peptide in this hydrolysable synthetic matrix [25, 30]. Considering the similar bioactivity of glycosylated and non-glycosylated rhBMP-2, understanding the differences in the release characteristics of these variants from the carrier materials and the effect of their interaction with the carrier materials on their bioactivity is crucial. This analysis would enable the development of a successful composite of these well-known materials that allows faster bone formation and more economical use of growth factors. We therefore investigated the differences between glycosylated and non-glycosylated rhBMP-2 in terms of their interactions with DBBM, hydrolysable PEG hydrogels, and the combination of these materials as well as the bioactivity of the released rhBMP-2 variants.

2 Materials and Methods

2.1 General Preparations

Non-glycosylated rhBMP-2 was expressed in *E.coli* and refolded as previously described [33]. Glycosylated rhBMP-2 was obtained from Genetics Institute Inc., Massachusetts, USA. Both rhBMP-2 variants were desalted by solvent exchange to 1 mM HCl using centrifugal filters (MWCO 10 kDa, Millipore, Zug, Switzerland). rhBMP-2 solutions were sterilized using Millex-LG Sterilizing Filter Units (0.2 μm , Millipore, Zug, Switzerland). The concentration of rhBMP-2 was determined by a Bradford assay (Thermo Fisher Scientific, Lausanne, Switzerland) and samples were diluted in 1 mM HCl to 1 $\mu\text{g}/\mu\text{l}$ accordingly.

All following experiments were carried out under sterile conditions and all materials were sterilized by vapour sterilization (134 °C) in the central sterilization facilities of the University Hospital Zurich unless specified separately. All experiments were carried out at room temperature (room temperature varied between 20 and 25 °C) unless specified separately. All samples were prepared with both glycosylated and non-glycosylated rhBMP-2.

2.2 Preparation of Bone Substitute Components

Hydrolyzable mPEG hydrogels were formed by a Michael-type reaction between acrylate and thiol groups described earlier by Elbert, et al. [31] and prepared similarly to previous *in vivo* studies [25, 30]. 15 kDa 4arm PEG functionalized with an acrylate group at the end of each arm and 3.8 kDa linear PEG dithiol dissolved in 1 mM HCl and gamma-sterilized were kindly provided by the Institute Straumann AG (Basel, Switzerland). Briefly, 50 μl PEG gels (unreacted volume) were formed in low binding microcentrifuge tubes (Eppendorf, Basel, Switzerland) in the presence or absence of

2.5 µg rhBMP-2 and/or 25 mg of DBBM (Bio Oss[®], small spongiosa granules 0.25 – 1 mm, gamma-sterilized, kindly provided by Geistlich Biomaterials, Wollhusen, Switzerland) by mixing acrylate and thiol PEGs in a 0.1 M triethanolamine solution. The volume of mPEG hydrogel was chosen to exactly cover the volume of the loose DBBM particles allowing a homogeneous distribution of DBBM in the hydrogel. The gelation reaction was allowed to take place for 30 min. In order to shorten the time periods for this study, the precursors were chosen for a final concentration of 3% (w/v) PEG allowing the mPEG hydrogel to hydrolyze completely after 3 days.

In order to adsorb rhBMP-2 to DBBM from solution, 25 mg of DBBM were mixed with 50 µl 1 mM HCl containing 2.5 µg rhBMP-2. The mixture was vortexed, briefly spun down (10600xg, 10s) in a centrifuge and incubated for 60 min. Samples were used immediately without removing the liquid from the adsorption procedure. For the adsorption of rhBMP-2 to DBBM via lyophilisation, 25 mg of DBBM were mixed with 50 µl 1 mM HCl containing 2.5 µg rhBMP-2. The mixture was vortexed, briefly spun down in a centrifuge (10600xg, 10s) and frozen immediately using liquid nitrogen. Frozen samples were lyophilized overnight. Controls were prepared without the addition of rhBMP-2. The pH change of 1 mM HCl solution 1h after the immersion of DBBM was evaluated using the same ratio between DBBM and 1 mM HCl as for the sample preparation.

2.3 Determination of rhBMP-2 Concentration Profiles

rhBM2-loaded samples and according controls were immersed in cell culture medium (Dulbecco's Modified Eagle Medium (D-MEM, Invitrogen, Basel, Switzerland) containing 10% inactivated fetal bovine serum (FBS, Invitrogen), 2 mM L-Glutamine (Invitrogen), 20 mM HEPES (stock adjusted to pH 7.4, SigmaAldrich, Buchs, Switzerland), 100 U/ml Penicillin and 100 µg/ml Streptomycin

(Penicillin/Streptomycin, Invitrogen)) resulting in a final volume of 500 μ l. The final sample volume was calculated including the hydrolyzable mPEG hydrogel (unreacted volume) as well as the liquid remaining in DBBM samples and controls but excluding the non-degradable (non-degradable regarding this time span) volume of DBBM. After preincubation for one hour in cell culture medium to allow initial adsorption of serum proteins, 2.5 μ g of rhBMP-2 were added to the controls. Positive controls of 500 μ l cell culture medium containing 2.5 μ g rhBMP-2 were prepared. Thus, all samples, controls and the positive controls contained 2.5 μ g rhBMP-2. Empty controls were prepared without the addition of rhBMP-2. An overview of all samples and controls as well as their abbreviations is shown in





condition	sample	control	empty control	positive control
mPEG rhBMP-2 incorporated in mPEG hydrogel				
DBBM rhBMP-2 adsorbed to DBBM				 rhBMP-2  DBBM
DBBM in mPEG rhBMP-2 and DBBM incorporated in mPEG hydrogel				 mPEG hydrogel  cell culture medium

Figure 1. All samples and controls were incubated at 37 °C for 15 days. 50 μ l supernatant were taken after 1h, 1, 2, 3, 6, 9 and 15 days of incubation and replaced by 50 μ l of fresh cell culture medium. The removed supernatant aliquots were stored at -20 °C for later analysis.

The concentration of rhBMP-2 in the supernatant was determined by an enzyme-linked immunosorbent assay (ELISA) against rhBMP-2 (R&D Systems, Quantikine BMP-2, Abingdon, UK). Standard series of glycosylated and non-glycosylated

rhBMP-2 were prepared to determine the rhBMP-2 concentration in the samples. The cumulative amount of released rhBMP-2 was calculated taking into account the removal and addition of 50 μ l of fresh medium at each time point. All results were standardized to the positive controls (100%).

2.4 Cell Culture Assays

2.4.1 Cell Stimulation

Glycosylated and non-glycosylated rhBMP-2 were tested for differences in their biological activity as well as for differences in their stability at 37 °C *in vitro*. Standard series (100 - 1000 ng/ml) of both rhBMP-2 variants were prepared in cell culture medium. The stability in cell culture medium was determined by incubating rhBMP-2 at 37 °C in cell culture medium for 0, 3, 9, 15 and 30 days without cells. A premyoblastic cell line (C2C12, ATCC, Molsheim Cedex, France) was stimulated with the standard series and the samples prepared for the stability test and tested for alkaline phosphatase activity as described in section 2.4.3.

The biological activity of the rhBMP-2 variants released from bone substitute materials as described in section 2.3 as well as the impact of bone substitute material degradation products and growth factors on cell viability were tested by stimulating C2C12 cells. Cells were stimulated with cell culture medium supernatant from a 15 days release from bone substitute materials prepared as described in section 2.3. Stimulated cells were tested for their viability as described in section 2.4.2 and for their ALP activity as described in section 2.4.3.

2.4.2 Cell Viability

Cell viability was evaluated after 3 and 6 days of incubation at 37 °C and 5% CO₂ in a humidified atmosphere. Viability was determined by adding cell proliferation

reagent WST-1 (Roche, Basel, Switzerland) to the cell culture medium at the concentration specified by the manufacturer. Cells were incubated in presence of the cell proliferation reagent for 45 min at 37 °C and 5 % CO₂. The resulting colour reaction was evaluated by measuring the optical density at 450 nm using a plate reader (Synergy HT, Biotek, Luzern, Switzerland).

2.4.3 Alkaline Phosphatase Activity

The biological activity of rhBMP-2 was determined via an assay for alkaline phosphatase (ALP) activity, an early marker for osteoblastic differentiation. ALP is expressed by mesenchymal progenitor cells exposed to rhBMP-2 and its activity therefore provides an appropriate functional assessment of the growth factors bioactivity [34]. In detail, C2C12 cells were stimulated for 6 days at 37 °C and 5 % CO₂ and were subsequently lysed using 0.56 M 2-Amino-2-methyl-1-propanol (SigmaAldrich, Buchs, Switzerland) (pH, 10 containing 0.2 % Triton X-100 (SigmaAldrich)). ALP activity in the lysis buffer was determined via the kinetics of a colour reaction based on the reduction of p-nitrophenyl phosphate (Sigma Aldrich) to p-nitrophenol. The DNA concentration of the lysate was determined using a PicoGreen assay (Invitrogen, Basel, Switzerland). Optical density of the p-nitrophenol reaction (410 nm) and fluorescence of PicoGreen (ex = 480 nm, em = 520 nm) was detected with a plate reader (Synergy HT, Biotek, Luzern, Switzerland). The determined ALP activity was adjusted to the total cell number by standardizing it to the DNA concentration. All results were standardized to the positive controls (100%).

2.5 Statistical Analysis

All experiments were carried out with a total number of 6 individual and independent samples for each condition ($n=6$), except for the ALP assay which was carried out with 12 independent samples ($n=12$). Each experiment was carried out twice. Gaussian distribution of samples was confirmed by a Shapiro-Wilk test. A two-tailed, heteroscedastic t-test ($P<0.05$) was applied to determine whether or not there are statistically significant differences between concentrations and/or activity of glycosylated and non-glycosylated rhBMP-2 after 15 days of incubation. For the statistical analysis of the cell culture viability, repeated measures ANOVA and subsequent pairwise Student's t-test with corrected P-values according to Bonferroni were used to detect significant differences between samples devoid of growth factors, loaded with non-glycosylated or glycosylated rhBMP-2.

3 Results

3.1 Interaction of rhBMP-2 with mPEG Hydrogels

Cumulative concentration of both glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of mPEG hydrogel samples was measured by an ELISA. The concentration of both growth factor variants increased up to day 3 and subsequently remained constant up to day 15 (

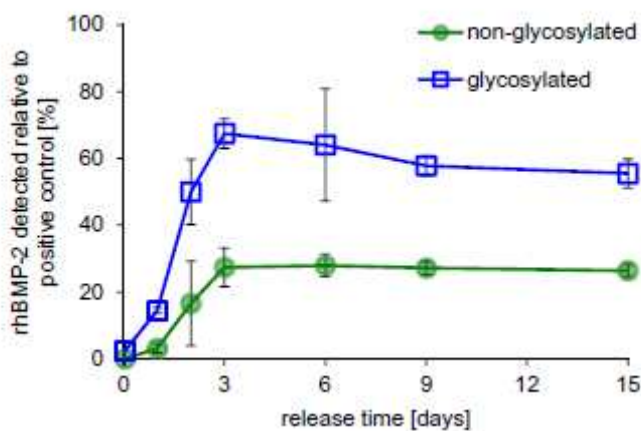


Figure 2). However, only part of the initial amount of rhBMP-2 was detected after 15 days of incubation time. We found significant differences between the concentration of glycosylated ($56 \pm 4\%$ of positive control) and non-glycosylated ($26 \pm 2\%$ of positive control) rhBMP-2 at day 15. A comparison of the mPEG hydrogel controls showed reduced concentrations of both rhBMP-2 variants. There was no significant change in concentration during the incubation time and there was no significant difference between the concentration of glycosylated ($58 \pm 11\%$ of positive control) and non-glycosylated ($56 \pm 5\%$ of positive control) rhBMP-2 at day 15 for the mPEG controls.

3.2 Interaction of rhBMP-2 with DBBM

pH measurements showed that the pH of 1 mM HCl was neutralized by DBBM after 1h if mixed at a concentration of 500 mg/ml DBBM (data not shown). We did not find any significant difference in adsorption behavior of rhBMP-2 between immersion in 1 mM HCl containing rhBMP-2 and lyophilisation (data not shown). We therefore applied the adsorption procedure without lyophilization for loading DBBM with rhBMP-2. After 1h adsorption in 1 mM HCl and 1h incubation in cell culture medium, $30 \pm 14\%$ glycosylated rhBMP-2 and $32 \pm 4\%$ non-glycosylated rhBMP-2 were detected in the cell culture medium supernatant relative to the positive control. These levels dropped to $7 \pm 3\%$ glycosylated and $16 \pm 7\%$ non-glycosylated rhBMP-2 after 15 days, showing a significant difference between the two growth factor variants (

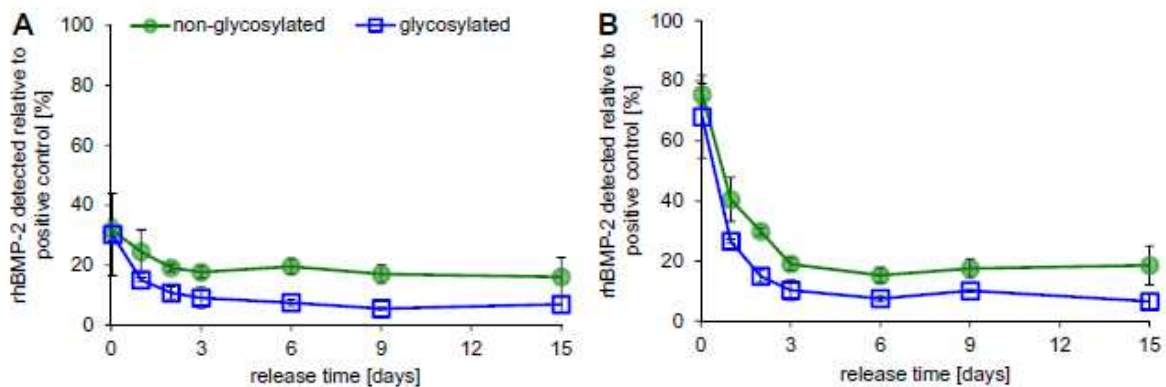


Figure 3 A). Concentrations of rhBMP-2 variants in the cell culture medium supernatant of DBBM controls showed a higher initial concentration than in the samples

(

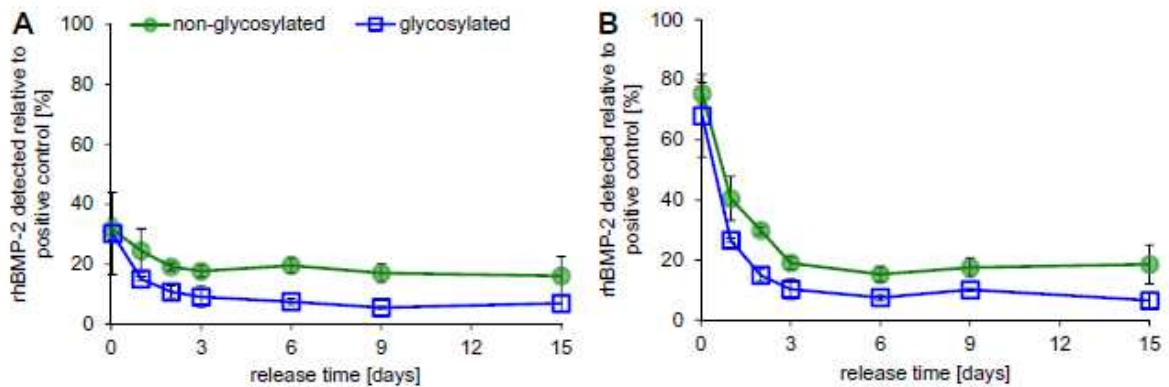


Figure 3 A & B). By day 3 of incubation the concentrations in the supernatant of the controls dropped to similar levels to the concentrations in the supernatant of the samples showing significant differences in concentration between glycosylated ($7 \pm 2\%$ of positive control) and non-glycosylated ($19 \pm 3\%$ of positive control) rhBMP-2 after 15 days.

3.3 Combination of mPEG hydrogel, DBBM and rhBMP-2

We detected strongly reduced concentrations of glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of DBBM in mPEG samples compared to the positive controls

(

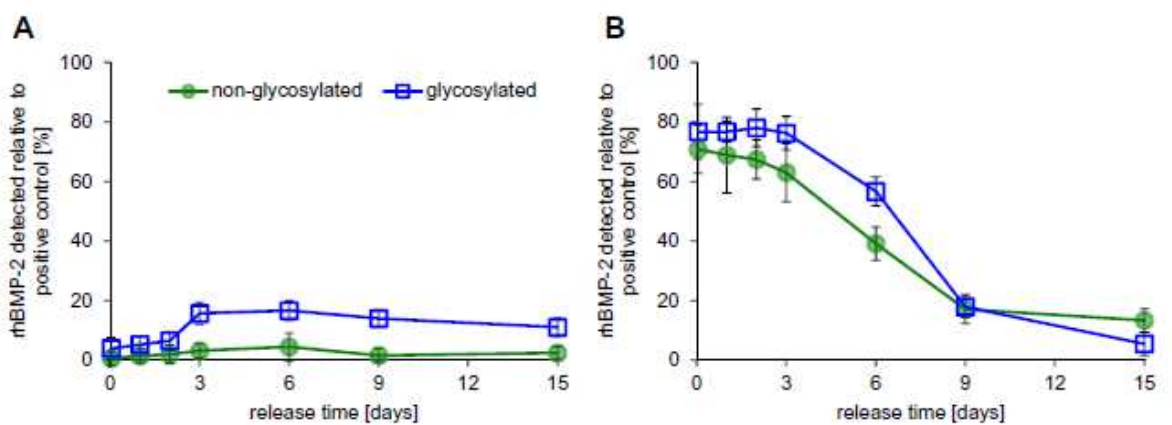


Figure 4 A). A maximum of $17 \pm 3\%$ glycosylated and $5 \pm 4\%$ non-glycosylated rhBMP-2 was detected after 6 days. After 15 days we found significant differences

between the concentration of glycosylated ($11 \pm 3\%$) and non-glycosylated ($3 \pm 2\%$) rhBMP-2. A high initial concentration of rhBMP-2 was found in the cell culture medium supernatant of the controls (

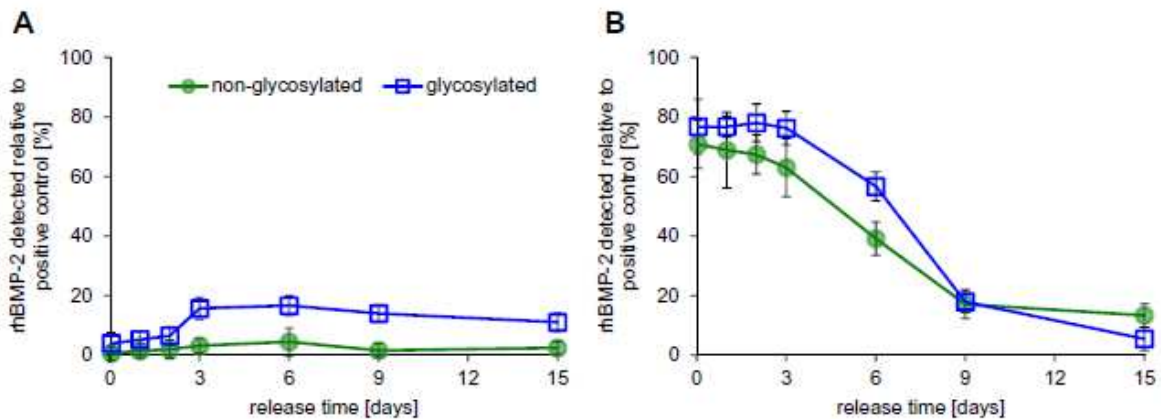


Figure 4 B). After 3 days we observed a quick drop of both the concentration of glycosylated and non-glycosylated rhBMP-2. After 15 days of incubation the concentration was found to be significantly higher for the non-glycosylated ($13 \pm 4\%$ of positive control) than for the glycosylated ($5 \pm 4\%$ of positive control) rhBMP-2.

3.4 Cell Viability - Influence of Degradation Products and rhBMP-2

C2C12 cells stimulated with the cell culture medium supernatant from all samples were tested for their cell viability. After three days, we found a significantly elevated cell viability comparing controls devoid of rhBMP-2 and samples with glycosylated rhBMP-2 in the positive controls and the DBBM sample group

(

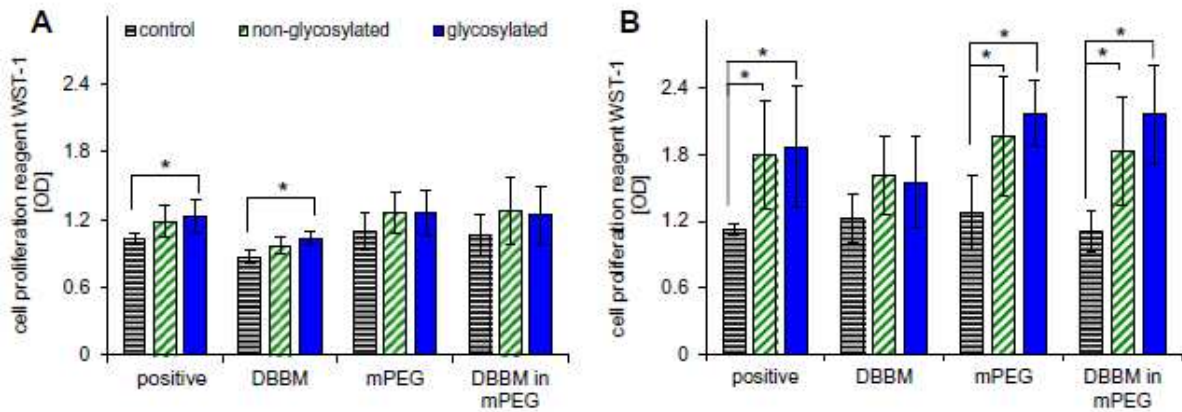


Figure 5 A). After 6 days, cell viability was significantly elevated in samples containing either glycosylated or non-glycosylated rhBMP-2 in the sample groups of positive controls, mPEG hydrogel and DBBM in mPEG hydrogel. There were no significant differences between samples containing glycosylated and non-glycosylated rhBMP-2

(

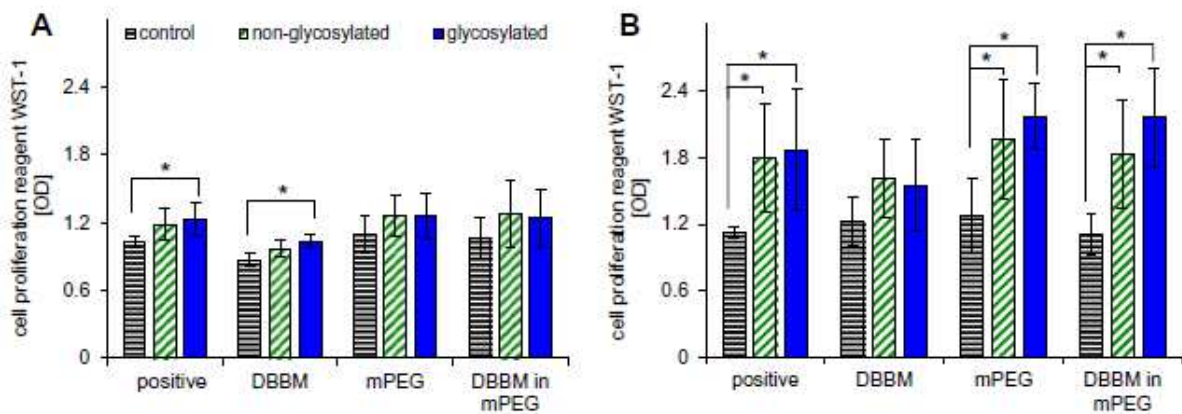


Figure 5 B). Comparing the cell viability between the bone substitute materials, we did not find any significant differences.

Along with the measurement of the biological activity of rhBMP-2 (section 2.4), we determined the total amount of DNA of the stimulated cells by a PicoGreen assay. After 6 days we found a significantly higher amount of DNA in samples containing

glycosylated or non-glycosylated rhBMP-2, however we did not find any significant differences between samples containing glycosylated or non-glycosylated rhBMP-2 (

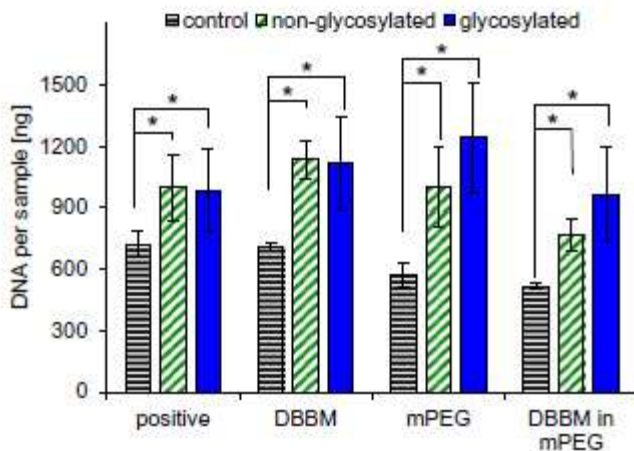


Figure 6). However, comparing the DNA content between samples stimulated with cell culture supernatant from bone substitute materials not containing rhBMP-2, we found a significant decrease for those samples containing mPEG hydrogels.

3.5 Biological Activity of rhBMP-2 – Impact of Bone Substitute Materials

The biological activity of glycosylated and non-glycosylated rhBMP-2 was tested by stimulating C2C12 cells with various concentrations of both growth variants and testing them for their ALP activity. We did not find any significant differences between glycosylated and non-glycosylated rhBMP-2

(

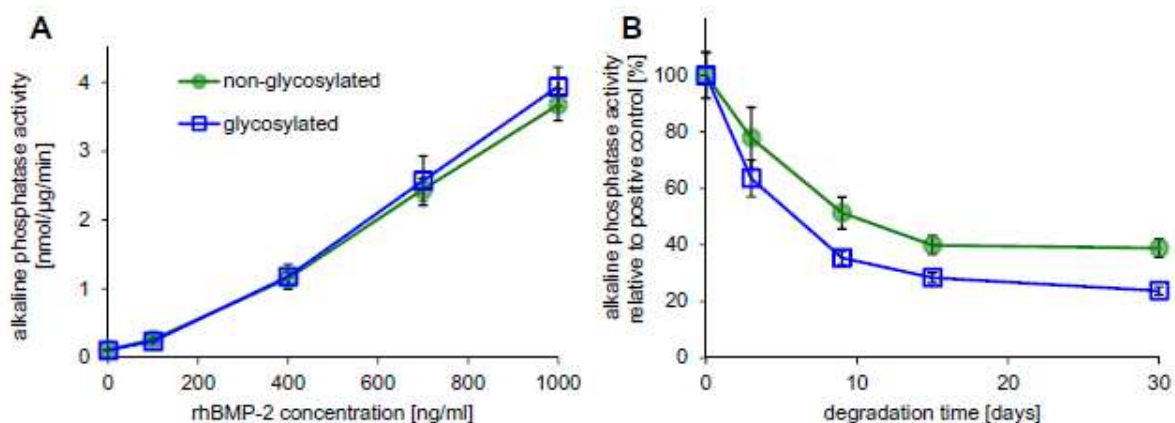


Figure 7 A). We found a strong decrease in ALP activity when stimulating C2C12 cells with rhBMP-2 preincubated for various times in cell culture medium at 37 °C and 5% CO₂

(

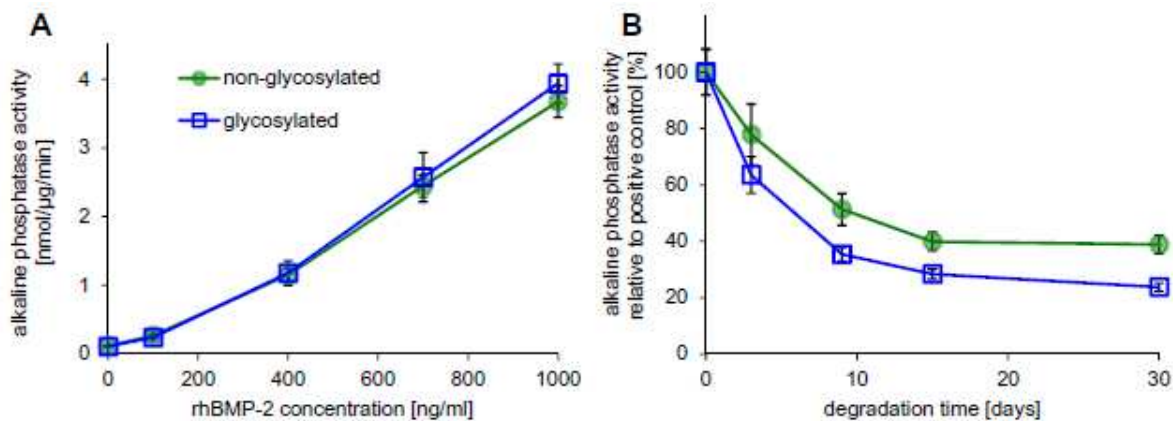


Figure 7 B). Glycosylated ($28 \pm 2\%$ initial activity) rhBMP-2 was significantly more affected than non-glycosylated ($40 \pm 3\%$ initial activity) rhBMP-2 after 30 days of preincubation.

The impact of incubating rhBMP-2 together with bone substitute materials on the bioactivity of the growth factor was investigated by stimulating C2C12 cells with the cell culture supernatant from mPEG hydrogels, DBBM and DBBM in mPEG hydrogel and testing them for their ALP activity. Incorporation into mPEG hydrogels reduced the activity of rhBMP-2 in the cell culture medium supernatant. The activity of non-glycosylated rhBMP-2 ($49 \pm 6\%$ of positive control) was reduced significantly more

than the activity of the glycosylated rhBMP-2 ($66 \pm 17\%$ of positive control) (


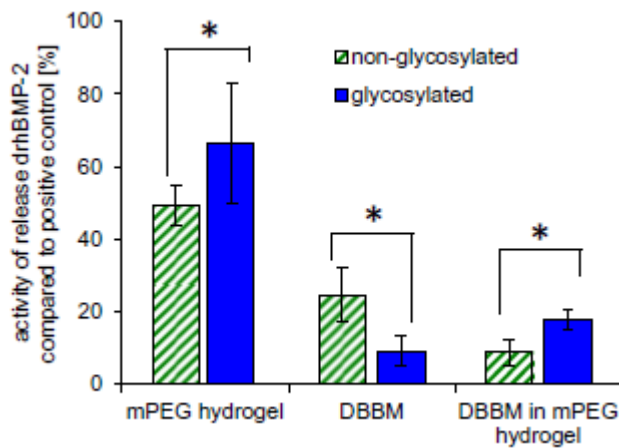


Figure 8). The activity of rhBMP-2 in the cell culture medium supernatant of DBBM was strongly decreased. This decrease was significantly higher for glycosylated ($9 \pm 4\%$ activity of positive control) than for non-glycosylated rhBMP-2 ($25 \pm 8\%$ activity of

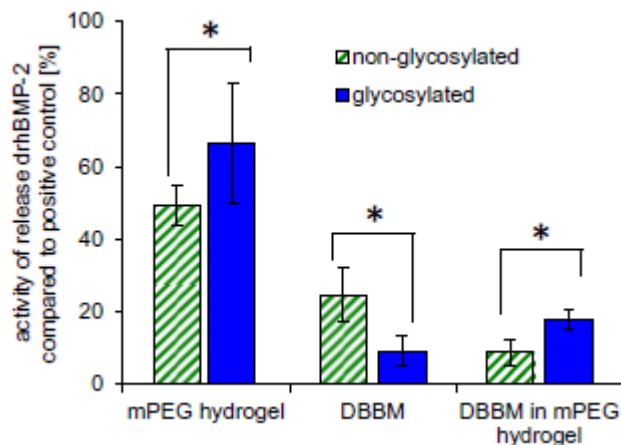

positive control) (

Figure 8). The activity of rhBMP-2 released from mPEG hydrogels having DBBM and rhBMP-2 incorporated was strongly decreased as well. The decrease was significantly higher for non-glycosylated ($9 \pm 3\%$ activity of positive control) than it

was for glycosylated rhBMP-2 ($18 \pm 3\%$ activity of positive control) (

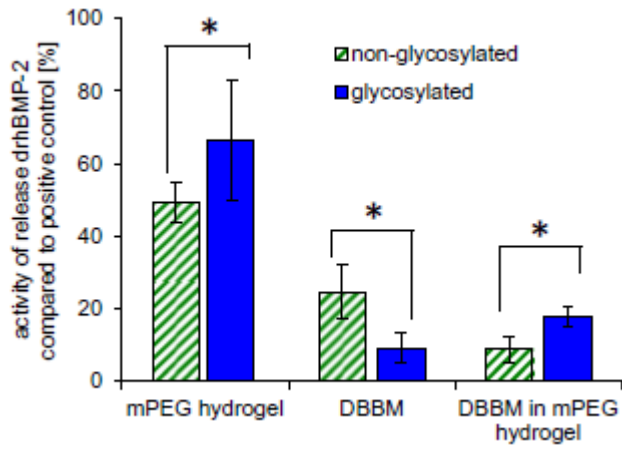


Figure 8).

4 Discussion

Our aim was to understand the differences between the interaction of glycosylated and non-glycosylated rhBMP-2 with clinically evaluated bone substitute materials. This analysis should ultimately allow for a combination of known materials and growth factors leading to an improved bone reconstruction. For our investigation we chose two well evaluated materials, mPEG hydrogels and DBBM. Both materials have previously been clinically tested for bone augmentation procedures in dentistry [7, 9, 25-30, 32].

We evaluated the equivalence of the two variants of rhBMP-2. In agreement with literature [9, 14-17], we found the biological activity of the glycosylated and non-glycosylated rhBMP-2 to be alike *in vitro* (

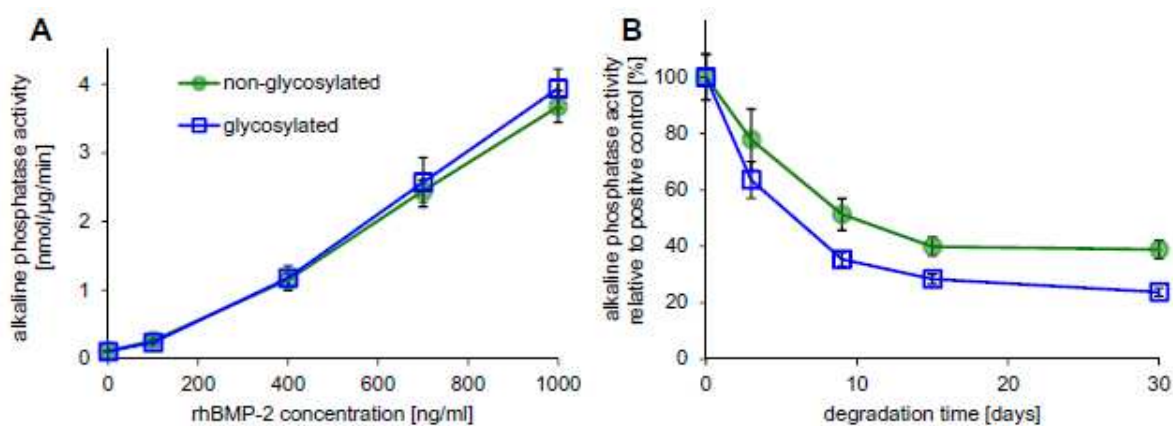


Figure 7). The biological activity of both variants drops rapidly in cell culture medium at 37 °C. This activity decrease has to be considered for rhBMP-2 delivery *in vivo* as well as for experimental design *in vitro*. Therefore, we compared all of our samples to a positive control of rhBMP-2 in cell culture medium. We further investigated equivalence of cell viability stimulated by the two variants of rhBMP-2. We observed a trend for an increase in cell viability in the presence of cell culture medium

supernatant from preincubated bone substitute materials and/or glycosylated or non-glycosylated rhBMP-2 after 3 days and found a significant increase after 6 days

(

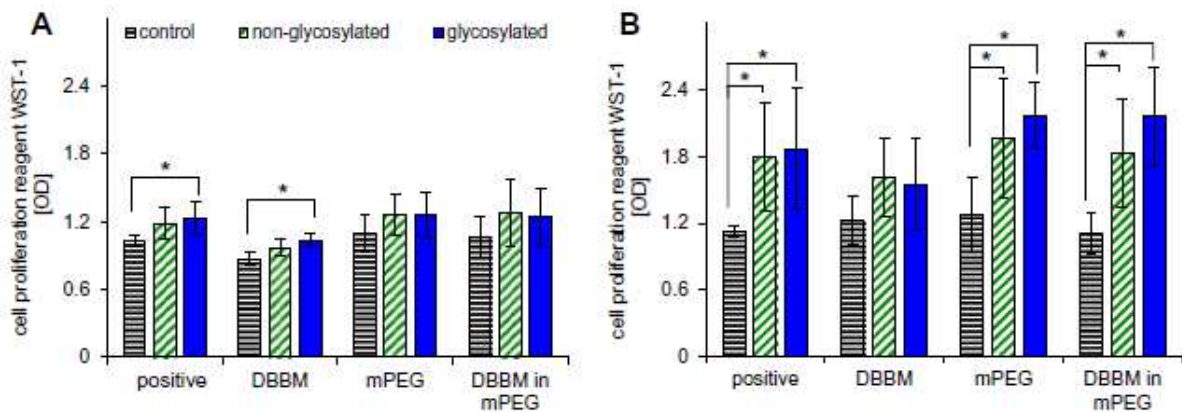


Figure 5 A & B). This increase in viability is reflected in the significantly higher total amount of DNA per sample in those samples containing rhBMP-2 (

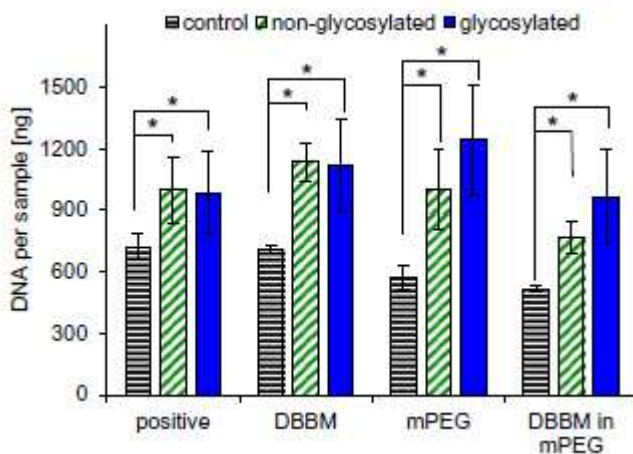


Figure 6) Our results agree with other work that shows the stimulation of cell viability by both glycosylated and non-glycosylated rhBMP-2 [17].

In investigating the effects of the mPEG hydrogel on the rhBMP-2 variants, we found that incorporating rhBMP-2 into an mPEG hydrogel reduces the amount of growth

factor detected in the cell culture medium supernatant (

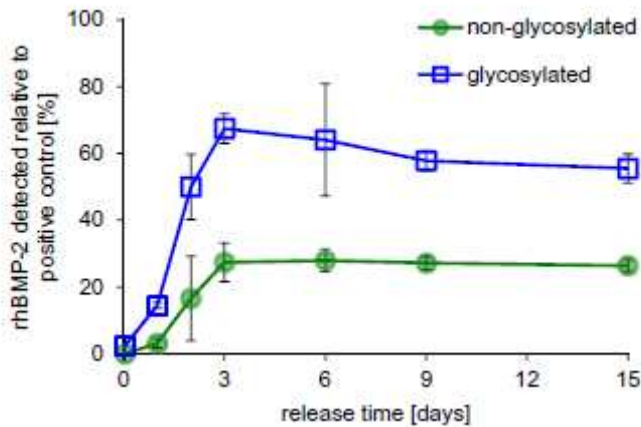


Figure 2) as well as the amount of active rhBMP-2 detected (

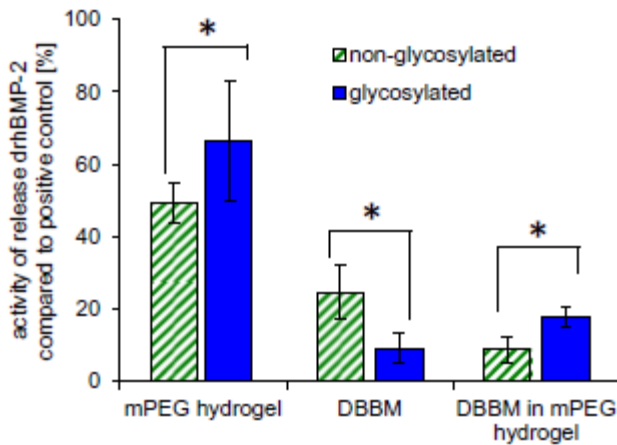


Figure 8) in the supernatant after 15 days of incubation. We hypothesize that this reduction is mainly caused by an interaction of rhBMP-2 with the PEG starting materials during gel formation. The thiol groups on the linear PEGs could attack the disulfide bonds of the rhBMP-2 dimers, leading to formation of monomers, incorrectly refolded dimers or even covalent incorporation of monomers into the mPEG hydrogel network. This hypothesis is supported by the significantly lower decrease in concentration of the glycosylated rhBMP-2, since the glycosylation can provide a protective effect. It is further supported by the fact that the concentration of non-glycosylated rhBMP-2 in the supernatant of the controls, where rhBMP-2 is added after mPEG hydrogel formation, is much higher than in the supernatant of the

corresponding control. However, it is possible that a weaker physical interaction between rhBMP-2 and remnants of the degraded mPEG hydrogel might be responsible for the reduced detection of rhBMP-2 in the controls. Although controlled PEGylation offers a great possibility to increase solubility and half-life of BMP-2 [35] or even allows for enzymatically controlled growth factor release [36] it should be avoided in order to deliver functional native rhBMP-2. Therefore, if applied together with an mPEG hydrogel, glycosylated rhBMP-2 is superior.

In contrast to the samples containing mPEG hydrogel, only a small part of the initial rhBMP-2 concentration can be detected in the cell culture medium supernatant of DBBM samples after 15 days of immersion. The amount of active rhBMP-2 detected in the cell culture medium supernatant is reduced to a corresponding amount. We attribute this effect to the high affinity of BMP-2 to hydroxyapatite-based materials [37] as well as to the high surface area (79.7 m²/g) of DBBM due to its micro- and nano-structure [38]. Moreover, instead of the expected release after immersion of DBBM preloaded with rhBMP-2, adsorption of rhBMP-2 continued even in the presence of serum proteins from the cell culture medium (

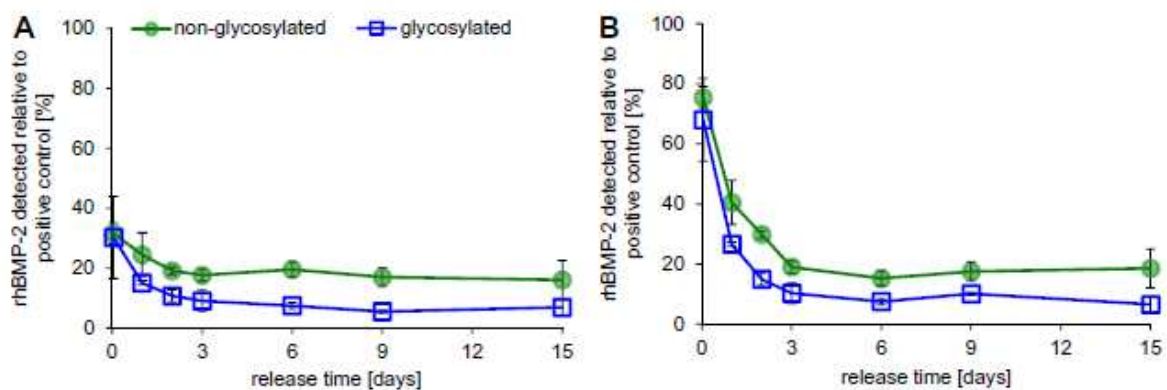


Figure 3 A). This result agrees with other work showing that the affinity of rhBMP-2 to hydroxyapatite is higher than the affinity of bovine serum albumin to

hydroxyapatite [37]. The reduced activity of the supernatant, however, does not necessarily imply a reduced activity *in vivo*, as indicated by successful studies on the combination of DBBM and rhBMP-2 [9, 32, 39]. rhBMP-2 could be adsorbed to DBBM in an active or a denatured form, or it could be that it is reactivated upon release after the slow degradation of DBBM *in vivo*. The significantly stronger affinity of glycosylated rhBMP-2 to DBBM compared to the non-glycosylated variant seems to recommend the use of glycosylated rhBMP-2 if applied together with DBBM. However, Brown et al. have shown *in vivo* that an initially high concentration of rhBMP-2 followed by a slow release is favourable over a slow release only [19]. This fact together with the much lower production costs for the expression of rhBMP-2 in *E.coli* makes non-glycosylated rhBMP-2 the preferred protein if applied together with DBBM. In the sole clinical trial where DBBM was used as carrier for non-glycosylated rhBMP-2 the results show that overall bone formation was not increased compared to DBBM alone but maturation of bone as well as direct coverage of DBBM by bone had advanced significantly [32]. Both results suggest that non-glycosylated rhBMP-2 delivered by DBBM is still active but the long range effect is limited due to the high affinity of rhBMP-2 to DBBM. Whether this remaining activity is due to the low amount of rhBMP-2 dissolved in the extracellular matrix, rhBMP-2 resolubilized after the slow dissolution of DBBM *in vivo* or rhBMP-2 adsorbed to DBBM cannot be determined based on these results.

Combining the two previously discussed materials we incorporated rhBMP-2 into mPEG hydrogels together with DBBM. This led to a constantly low concentration of rhBMP-2 in the cell culture medium supernatant during the 15 days of incubation, with a small increase after three days. After 15 days, in contrast to the samples with DBBM alone, a significantly higher concentration of glycosylated compared to non-

glycosylated rhBMP-2 can be detected

(

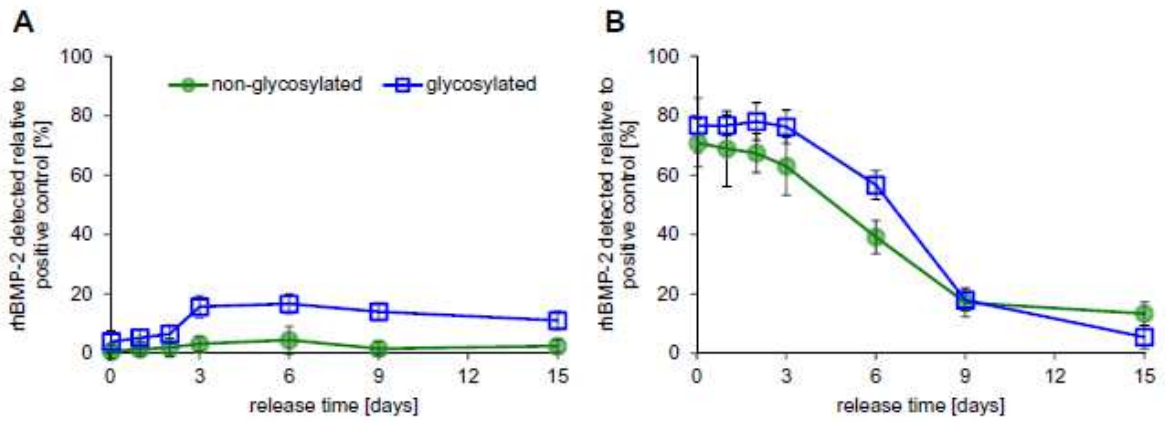


Figure 4 A). This result is confirmed by cell culture experiments that show the same significant difference for the amount of active rhBMP-2 detectable in the cell culture medium supernatant (

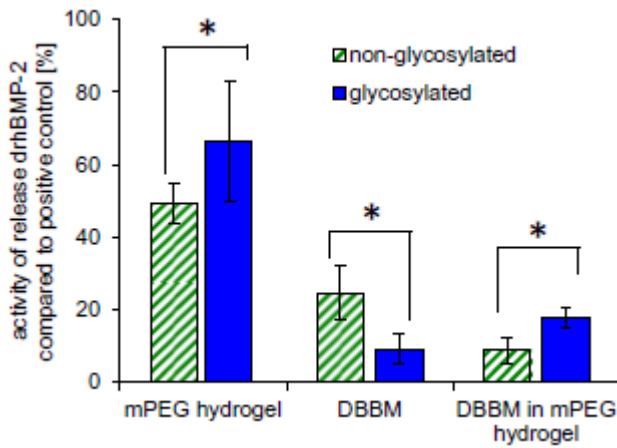


Figure 8). We attribute this to the reduced detectability of non-glycosylated rhBMP-2 if present during formation of mPEG hydrogels (

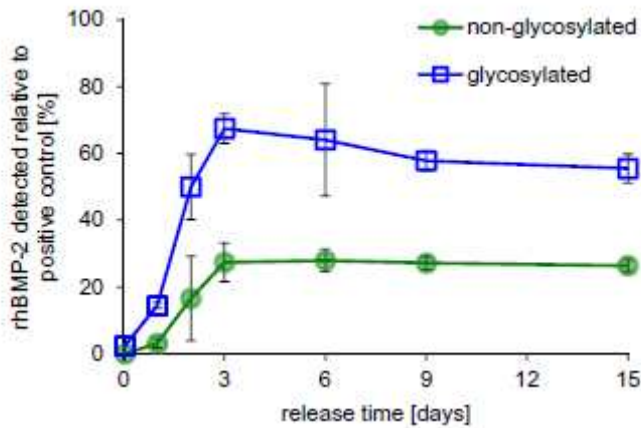


Figure 2). Control samples for DBBM in mPEG hydrogels initially only show a small decrease in rhBMP-2 concentration in the cell culture medium supernatant. However, the concentration drops drastically after three days (

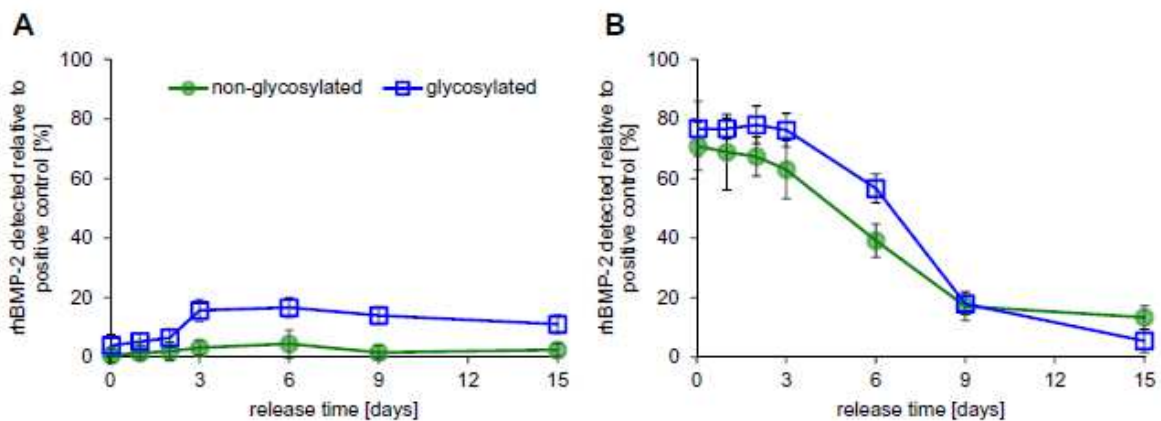


Figure 4 B). This drop can be explained with the hydrolyzation of the mPEG hydrogel that was covering the DBBM, leading to an adsorption of rhBMP-2 to DBBM. The concentration of non-glycosylated rhBMP-2 is, in agreement with the results for DBBM alone, significantly higher than for glycosylated rhBMP-2, supporting the assumption that the only reason for the lower concentration of non-glycosylated

rhBMP-2 in the samples is due to its interaction with the mPEG hydrogel components during hydrogel formation.

5 Conclusions

We have shown that mPEG hydrogels interact with rhBMP-2 and reduce its activity. Furthermore, we found a strong affinity of rhBMP-2 to DBBM. Based on these results we question the use of mPEG hydrogels as a carrier-system for rhBMP-2 in conjunction with DBBM, since the use of DBBM with preadsorbed rhBMP-2 alone yields a higher BMP activity, which might translate to better results *in vivo*. Since the affinity of non-glycosylated rhBMP-2 to DBBM is lower than the affinity of the glycosylated variant, non-glycosylated rhBMP-2 may be used if an initial high concentration of rhBMP-2 is desired to attract cells chemotactically. Further research on this aspect is necessary to determine if rhBMP-2 adsorbed to DBBM and hydroxyapatite in general is active or denatured and/or released in an active form during degradation. However if other needs, e.g. formability or stability of the bone substitute require the use of mPEG hydrogels, glycosylated rhBMP-2 is the preferred growth factor since its interactions with mPEG hydrogels is significantly lower compared to non-glycosylated rhBMP-2.

Acknowledgements

This study was financially supported by an ITI research grant of the ITI foundation (555-2007) and in part supported by AOCMF (project: C-10-37W), the Craniomaxillofacial Specialty of the AO Foundation. We thank the Institut Straumann AG for providing us with the mPEG precursors.

References

- [1] Sommerfeldt DW, Rubin CT. Biology of bone and how it orchestrates the form and function of the skeleton. *Eur Spine J* 2001;10 Suppl 2:S86-95.
- [2] Sailer HF, Weber FE. [Bone substitutes]. *Mund Kiefer Gesichtschir* 2000;4 Suppl 1:S384-91.
- [3] Cornell CN. Osteobiologics. *Bull Hosp Jt Dis* 2004;62:13-7.
- [4] Giannoudis PV, Einhorn TA, Schmidmaier G, Marsh D. The diamond concept--open questions. *Injury* 2008;39 Suppl 2:S5-8.
- [5] Jager M, Westhoff B, Wild A, Krauspe R. [Bone harvesting from the iliac crest]. *Orthopade* 2005;34:976-82, 84, 86-90, 92-4.
- [6] Nicoll SB. *Materials for Bone Graft Substitutes and Osseous Tissue Regeneration*: Springer; 2011.
- [7] Sartori S, Silvestri M, Forni F, Icaro Cornaglia A, Tesei P, Cattaneo V. Ten-year follow-up in a maxillary sinus augmentation using anorganic bovine bone (Bio-Oss). A case report with histomorphometric evaluation. *Clin Oral Implants Res* 2003;14:369-72.
- [8] Urist MR. Bone: formation by autoinduction. *Science* 1965;150:893-9.
- [9] Jung RE, Glauser R, Scharer P, Hammerle CH, Sailer HF, Weber FE. Effect of rhBMP-2 on guided bone regeneration in humans. *Clin Oral Implants Res* 2003;14:556-68.
- [10] Wozney JM, Rosen V, Celeste AJ, Mitscock LM, Whitters MJ, Kriz RW, et al. Novel regulators of bone formation: molecular clones and activities. *Science* 1988;242:1528-34.
- [11] Sampath TK, Maliakal JC, Hauschka PV, Jones WK, Sasak H, Tucker RF, et al. Recombinant human osteogenic protein-1 (hOP-1) induces new bone formation in vivo with a specific activity comparable with natural bovine osteogenic protein and stimulates osteoblast proliferation and differentiation in vitro. *J Biol Chem* 1992;267:20352-62.
- [12] Wildemann B, Burkhardt N, Luebberstedt M, Vordemvenne T, Schmidmaier G. Proliferating and differentiating effects of three different growth factors on pluripotent mesenchymal cells and osteoblast like cells. *J Orthop Surg Res* 2007;2:27.
- [13] McKay WF, Peckham SM, Badura JM. A comprehensive clinical review of recombinant human bone morphogenetic protein-2 (INFUSE Bone Graft). *Int Orthop* 2007;31:729-34.
- [14] Bessho K, Konishi Y, Kaihara S, Fujimura K, Okubo Y, Iizuka T. Bone induction by Escherichia coli -derived recombinant human bone morphogenetic protein-2 compared with Chinese hamster ovary cell-derived recombinant human bone morphogenetic protein-2. *Br J Oral Maxillofac Surg* 2000;38:645-9.
- [15] Lee JH, Kim CS, Choi KH, Jung UW, Yun JH, Choi SH, et al. The induction of bone formation in rat calvarial defects and subcutaneous tissues by recombinant human BMP-2, produced in Escherichia coli. *Biomaterials* 2010;31:3512-9.
- [16] Ruppert R, Hoffmann E, Sebald W. Human bone morphogenetic protein 2 contains a heparin-binding site which modifies its biological activity. *Eur J Biochem* 1996;237:295-302.
- [17] Kim IS, Lee EN, Cho TH, Song YM, Hwang SJ, Oh JH, et al. Promising Efficacy of Escherichia coli Recombinant Human Bone Morphogenetic Protein-2 in Collagen Sponge for Ectopic and Orthotopic Bone Formation and Comparison with Mammalian Cell Recombinant Human Bone Morphogenetic Protein-2. *Tissue Eng Part A* 2011;17:337-48.
- [18] Cho TJ, Gerstenfeld LC, Einhorn TA. Differential temporal expression of members of the transforming growth factor beta superfamily during murine fracture healing. *J Bone Miner Res* 2002;17:513-20.
- [19] Brown KV, Li B, Guda T, Perrien DS, Guelcher S, Wenke JC. Improving Bone Formation in a Rat Femur Segmental Defect by Controlling BMP-2 Release. *Tissue Eng Part A* 2011.
- [20] Sigurdsson TJ, Nygaard L, Tatakis DN, Fu E, Turek TJ, Jin L, et al. Periodontal repair in dogs: evaluation of rhBMP-2 carriers. *Int J Periodontics Restorative Dent* 1996;16:524-37.
- [21] Hunt DR, Jovanovic SA, Wikesjo UM, Wozney JM, Bernard GW. Hyaluronan supports recombinant human bone morphogenetic protein-2 induced bone reconstruction of advanced alveolar ridge defects in dogs. A pilot study. *J Periodontol* 2001;72:651-8.
- [22] Kim CS, Kim JI, Kim J, Choi SH, Chai JK, Kim CK, et al. Ectopic bone formation associated with recombinant human bone morphogenetic proteins-2 using absorbable collagen sponge and beta tricalcium phosphate as carriers. *Biomaterials* 2005;26:2501-7.
- [23] Hong SJ, Kim CS, Han DK, Cho IH, Jung UW, Choi SH, et al. The effect of a fibrin-fibronectin/beta-tricalcium phosphate/recombinant human bone morphogenetic protein-2 system on bone formation in rat calvarial defects. *Biomaterials* 2006;27:3810-6.

- [24] Jung UW, Choi SY, Pang EK, Kim CS, Choi SH, Cho KS. The effect of varying the particle size of beta tricalcium phosphate carrier of recombinant human bone morphogenetic protein-4 on bone formation in rat calvarial defects. *J Periodontol* 2006;77:765-72.
- [25] Jung RE, Hammerle CH, Kokovic V, Weber FE. Bone regeneration using a synthetic matrix containing a parathyroid hormone peptide combined with a grafting material. *Int J Oral Maxillofac Implants* 2007;22:258-66.
- [26] Jung RE, Windisch SI, Eggenschwiler AM, Thoma DS, Weber FE, Hammerle CH. A randomized-controlled clinical trial evaluating clinical and radiological outcomes after 3 and 5 years of dental implants placed in bone regenerated by means of GBR techniques with or without the addition of BMP-2. *Clin Oral Implants Res* 2009;20:660-6.
- [27] Jung RE, Lecloux G, Rompen E, Ramel CF, Buser D, Hammerle CH. A feasibility study evaluating an in situ formed synthetic biodegradable membrane for guided bone regeneration in dogs. *Clin Oral Implants Res* 2009;20:151-61.
- [28] Herten M, Jung RE, Ferrari D, Rothamel D, Golubovic V, Molenberg A, et al. Biodegradation of different synthetic hydrogels made of polyethylene glycol hydrogel/RGD-peptide modifications: an immunohistochemical study in rats. *Clin Oral Implants Res* 2009;20:116-25.
- [29] Thoma DS, Halg GA, Dard MM, Seibl R, Hammerle CH, Jung RE. Evaluation of a new biodegradable membrane to prevent gingival ingrowth into mandibular bone defects in minipigs. *Clin Oral Implants Res* 2009;20:7-16.
- [30] Jung RE, Weber FE, Thoma DS, Ehrbar M, Cochran DL, Hammerle CH. Bone morphogenetic protein-2 enhances bone formation when delivered by a synthetic matrix containing hydroxyapatite/tricalciumphosphate. *Clin Oral Implants Res* 2008;19:188-95.
- [31] Elbert DL, Pratt AB, Lutolf MP, Halstenberg S, Hubbell JA. Protein delivery from materials formed by self-selective conjugate addition reactions. *J Control Release* 2001;76:11-25.
- [32] Jung RE, Halg GA, Thoma DS, Hammerle CH. A randomized, controlled clinical trial to evaluate a new membrane for guided bone regeneration around dental implants. *Clin Oral Implants Res* 2009;20:162-8.
- [33] Weber FE, Eyrich G, Gratz KW, Maly FE, Sailer HF. Slow and continuous application of human recombinant bone morphogenetic protein via biodegradable poly(lactide-co-glycolide) foamspheres. *Int J Oral Max Surg* 2002;31:60-5.
- [34] Katagiri T, Yamaguchi A, Komaki M, Abe E, Takahashi N, Ikeda T, et al. Bone morphogenetic protein-2 converts the differentiation pathway of C2C12 myoblasts into the osteoblast lineage. *J Cell Biol* 1994;127:1755-66.
- [35] Hu J, Duppatla V, Harth S, Schmitz W, Sebald W. Site-specific PEGylation of bone morphogenetic protein-2 cysteine analogues. *Bioconjug Chem* 2010;21:1762-72.
- [36] Ehrbar M, Rizzi SC, Schoenmakers RG, Miguel BS, Hubbell JA, Weber FE, et al. Biomolecular hydrogels formed and degraded via site-specific enzymatic reactions. *Biomacromolecules* 2007;8:3000-7.
- [37] Boix T, Gomez-Morales J, Torrent-Burgues J, Monfort A, Puigdomenech P, Rodriguez-Clemente R. Adsorption of recombinant human bone morphogenetic protein rhBMP-2m onto hydroxyapatite. *J Inorg Biochem* 2005;99:1043-50.
- [38] Weibrich G, Trettin R, Gnoth SH, Gotz H, Duschner H, Wagner W. [Determining the size of the specific surface of bone substitutes with gas adsorption]. *Mund Kiefer Gesichtschir* 2000;4:148-52.
- [39] Kubler NR, Wurzler KK, Reuther JF, Sieber E, Kirchner T, Sebald W. [Effect of different factors on the bone forming properties of recombinant BMPs]. *Mund Kiefer Gesichtschir* 2000;4 Suppl 2:S465-9.

6 Figures

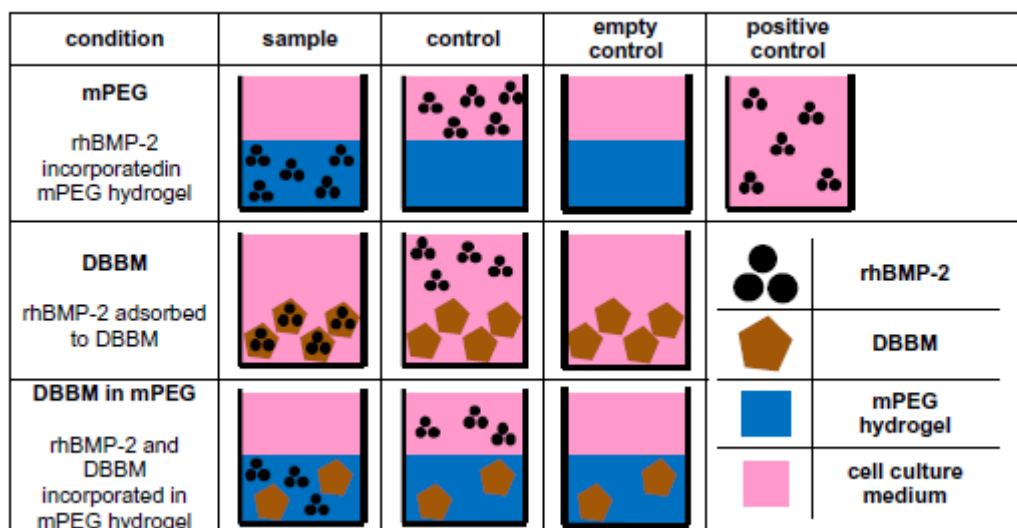


Figure 1: Scheme of experimental setups. Glycosylated and non-glycosylated rhBMP-2 was incorporated into mPEG hydrogels, adsorbed to DBBM and incorporated into an mPEG hydrogel together with DBBM. These samples were immersed in cell culture medium to investigate concentration and activity in the supernatant over time. In order to separate effects derived from the adsorption or incorporation procedures, controls devoid of rhBMP-2 were prepared and immersed in cell culture medium that was subsequently supplemented with rhBMP-2. Empty controls without rhBMP-2 were prepared in order to evaluate the effect of the bone substitute material degradation products on cell viability. The low biological half-life of rhBMP-2 was taken into account by comparing all results to a positive control of rhBMP-2 in cell culture medium.

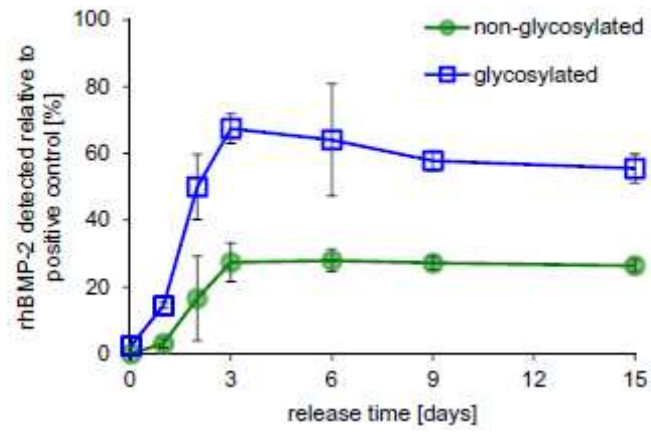


Figure 2. Concentration of glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of mPEG samples detected by an ELISA.

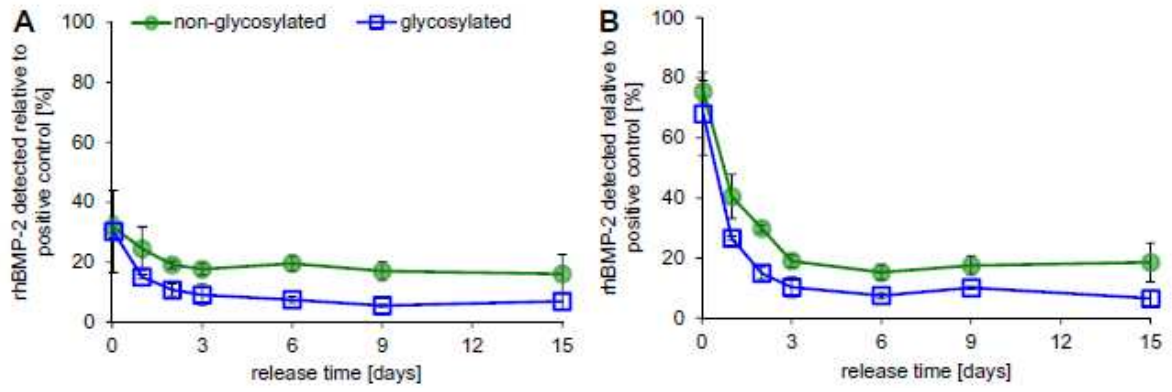


Figure 3. Concentration of glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of DBBM samples and controls detected by an ELISA. A) DBBM samples. B) DBBM controls.

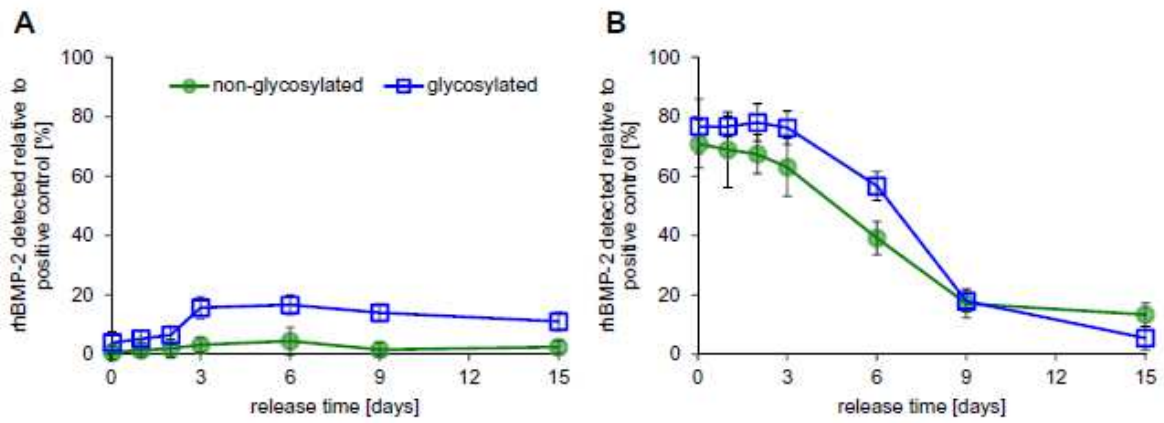


Figure 4. Concentration of glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of DBBM in mPEG samples and controls detected by an ELISA. A) DBBM in mPEG samples B) DBBM in mPEG controls.

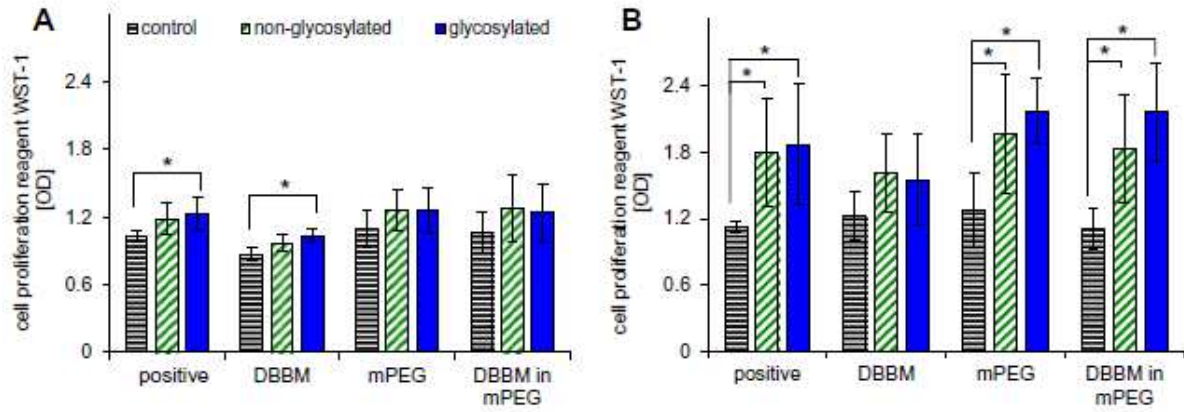


Figure 5: Cell viability of C2C12 cells stimulated with cell culture medium supernatant from mPEG, DBBM and DBBM in mPEG measured by cell proliferation reagent WST-1. A) After 3 days of stimulation. B) After 6 days of stimulation. An asterisk indicates a significant difference between samples ($p < 0.05$)

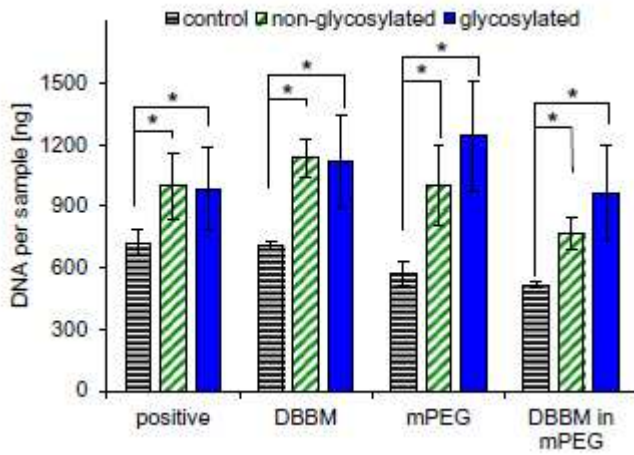


Figure 6: DNA concentration per sample of cells stimulated with cell culture medium supernatant from mPEG, DBBM and DBBM in mPEG hydrogel samples determined by a PicoGreen assay. An asterisk indicates a significant difference between samples ($p < 0.05$)

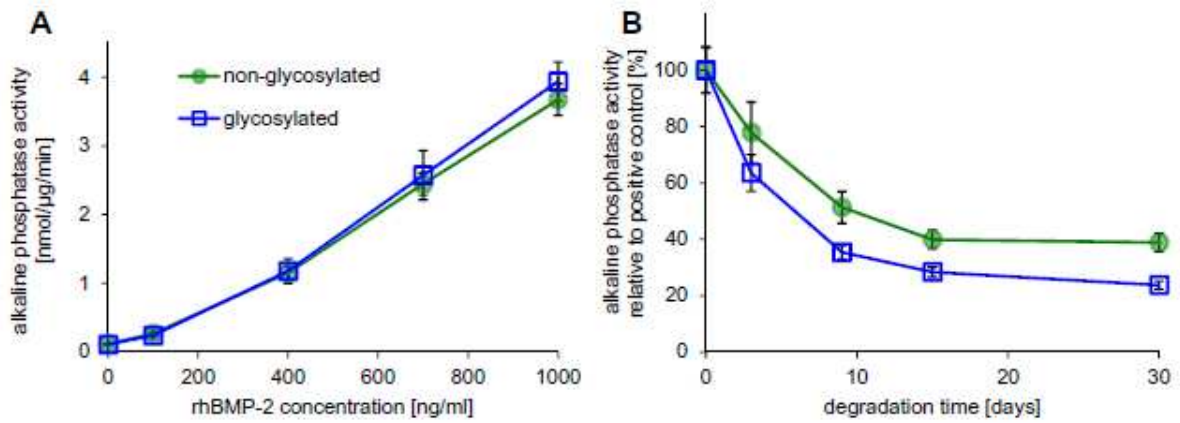


Figure 7: Bioactivity and stability of non-glycosylated and glycosylated rhBMP-2. A) ALP activity of cells stimulated by various concentrations of non-glycosylated and glycosylated rhBMP-2. B) ALP activity of cells stimulated with rhBMP-2 preincubated for various time spans at 37 °C in cell culture medium.

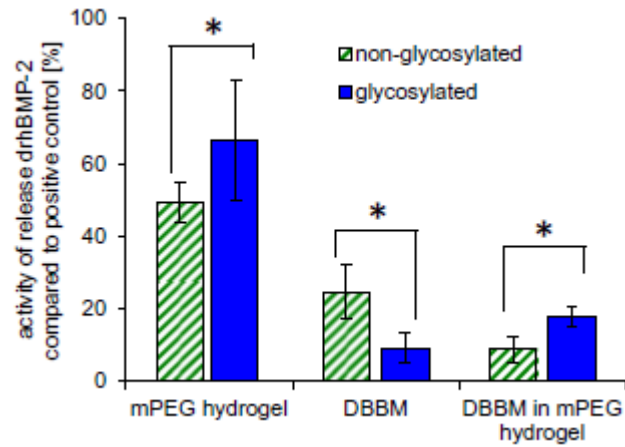


Figure 8: Bioactivity of glycosylated and non-glycosylated rhBMP-2 in the cell culture medium supernatant of mPEG, DBBM and DBBM in mPEG samples after 15 days of incubation. C2C12 cells were stimulated with cell culture medium supernatant from the samples and incubated for 6 days followed by an ALP activity assay.